

Bands renormalization and superconductivity in the strongly correlated Hubbard model using composite operators method

L. Haurie,¹ M. Grandadam,² E. Pangburn,¹ A. Banerjee,³ S. Burdin,⁴ and C. Pépin¹

¹*Institut de Physique Théorique, Université Paris Saclay,
CEA CNRS, Orme des Merisiers, 91190 Gif-sur-Yvette Cedex, France*

²*Department of Physics and Physical Oceanography,
Memorial University of Newfoundland, St. John's,
Newfoundland & Labrador, Canada A1B 3X7*

³*Department of Physics, Ben-Gurion University of the Negev, Beer-Sheva 84105, Israel*

⁴*Université de Bordeaux, CNRS, LOMA, UMR 5798, F-33400 Talence, France*

(Dated: May 16, 2023)

We use the composite operator method (COM) to analyze the strongly correlated repulsive Hubbard model, investigating the effect of nearest-neighbor hoppings up to fourth order on a square lattice. We consider two sets of self-consistent equations, one enforcing the Pauli principle and the other imposing charge-charge, spin-spin, and pair-pair correlations using a decoupling scheme developed by L. Roth [Phys. Rev. **184**, 451–459, (1969)]. We extract three distinct solutions from these equations: COM1 and COM2 by imposing the Pauli principle and one from Roth decoupling. An overview of the method studying the validity of particle-hole symmetry and the Luttinger theorem for each solution is presented. Additionally, we extend the initial basis to study superconductivity, concluding that it is induced by the Van Hove singularity. Finally, we include higher-order hoppings using realistic estimates for tight binding parameters and compare our results with ARPES measurements on cuprates.

I. INTRODUCTION

Exotic behavior and multiple phases exhibited by strongly correlated materials have attracted significant interest in the quantum condensed matter community [1, 2]. One prominent example is cuprates, where superconductivity survives up to very high critical temperatures compared to conventional superconductors described by the BCS theory [3]. Since their discovery in 1987 by G. Bednorz and K.A. Müller [4], extensive research has focused on modeling and understanding the pairing mechanism in these materials to obtain a microscopic theory of cuprate superconductors. The complexity of their phase diagram and the numerous unexplained quantum phases [5] have resulted in various theoretical models [6].

The repulsive Hubbard model remains the paradigmatic tool for studying strongly correlated quantum matter even after sixty years of its proposal. It offers a minimal description of such systems with just two ingredients - hopping of electrons between lattice sites t and on-site electron repulsion U creating an energy cost for double occupancy on the same lattice site. It is given by

$$H = - \sum_{i,j\sigma} t_{ij} c_{i\sigma}^\dagger c_{j\sigma} + U \sum_i n_{i\uparrow} n_{i\downarrow} + \mu \sum_{i\sigma} n_{i\sigma}, \quad (1)$$

where the chemical potential μ fixes the total number of electrons. In Eq. (1) t_{ij} is such that $t_{ij} = t$ if i and j are nearest neighbouring sites, and zero otherwise. One can extend the model to longer ranged hoppings. $c_{i\sigma}/c_{i\sigma}^\dagger$ destroys/creates an electron on site i with spin $\sigma \in \{\uparrow, \downarrow\}$ on the lattice and $n_{i\sigma} = c_{i\sigma}^\dagger c_{i\sigma}$ is the number operator for site i and spin σ . However, this seemingly straightforward model has eluded unbiased theoretical solutions.

The Hubbard Hamiltonian is known to be solvable only in one dimension (1d) and infinite dimensions [7]. In the intermediate dimensions, the equations of motion of the electronic Green's function involve higher order Green's function and cannot be solved exactly [8]. In the past, approximations such as Hubbard I and II (Ref. [8]) have been made to truncate the higher-order terms and close the equations of motion.

We revisit a perturbative scheme called "Composite Operators Method" (COM) [9] [10], which was developed to close the equations of motion of the electronic Green's function of the Hubbard model to derive sets of self-consistent equations. We consider two sets of such self-consistency equations. The first enforces charge-charge, spin-spin, and pair-pair correlations using L. Roth's decoupling scheme [11], and the second imposes the Pauli principle instead of correlations. We perform a numerical minimization

of these two sets of equations. The self-consistency equations enforcing the Pauli principle yield two distinct solutions named COM1 and COM2. The other sets of equations using Roth decoupling only exhibit one solution, which is referred to as the Roth solution. Despite violating the Pauli principle [9], the Roth solution shows a band structure in agreement with quantum Monte-Carlo simulations [10]. In contrast, COM1 and COM2, which have been studied more widely, exhibit a Fermi surface consistent with cuprate ARPES experiments only under some approximations [12].

Although the self-consistency equations enforcing the Pauli principle have been previously minimized with next-nearest neighbor hoppings [13], this is not the case for the Roth decoupling. The latter has been studied with next-nearest neighbor hoppings for a three-band Hubbard model in cuprates [14], but never for the one-orbital Hubbard model.

Superconductivity has also been studied using the COM[10]. Past studies indicate that the proximity to the Van Hove singularity enhances SC within Roth minimization scheme [15]. The enhancement of the density of the state associated with this singularity allows electrons to form more pairs readily. However, a detailed study comparing and contrasting different self-consistent solutions and including realistic hopping parameters to model the cuprates is still lacking.

The objective of this study is to analyze the strongly correlated regime of the Hubbard model where $|U| \gg t$ using the composite operators method. We aim to compare and contrast the solutions obtained in previous studies using the COM. We evaluate their physical consistency with experiments in cuprates by testing the particle-hole symmetry and the validity Luttinger theorem. Finally, we include the superconductivity with longer-ranged hoppings. The plan for the rest of the paper is as follows: Section II details the formalism and self-consistency we use in the manuscript. In section III, we restrict to the nearest neighbor hoppings and compare the solutions obtained by the different minimizations [10] [16] while discussing their physical implications, particularly with regard to particle-hole symmetry and the Luttinger theorem. Finally, we allow for the superconductivity in the model, and in the last section IV, we study the impact of the longer-ranged hopping orders.

II. COMPOSITE OPERATOR FORMALISM

Composite operators are introduced in order to solve exactly the equations of motion of composite Green's functions (Green's functions composed of two composite operators) in some limits. Since we are interested in a strongly correlated regime of Hubbard model, we introduce composite operators solving exactly the Hubbard model in the atomic limit (no hopping term). This is a good starting point to treat the hopping term t with a perturbation expansion.

A. Presentation of the method

We start by introducing the following composite operators

$$\begin{cases} \xi_{i\sigma} &= c_{i\sigma} - c_{i\sigma} n_{i\bar{\sigma}} \\ \eta_{i\sigma} &= c_{i\sigma} n_{i\bar{\sigma}} \end{cases} \quad (2)$$

Where $\bar{\sigma}$ means we take a spin \uparrow if $\sigma = \downarrow$ and a spin \downarrow if $\sigma = \uparrow$. We introduce the following spinors

$$\psi_{i\sigma} = \begin{pmatrix} \xi_{i\sigma} \\ \eta_{i\sigma} \end{pmatrix} \quad (3)$$

Hereafter, $\psi_{i\sigma}^1 = \xi_{i\sigma}$ and $\psi_{i\sigma}^2 = \eta_{i\sigma}$ denotes the first and second component of the spinor at site i and with spin σ .

1. Atomic limit

To illustrate the interest of introducing these operators, we first consider the atomic limit of Eq. (1): we put the hopping term t to zero. The Hamiltonian is now local (ie electrons are not hopping anymore and each site is independent) and is given by

$$H_{loc} = U \sum_i n_{i\uparrow} n_{i\downarrow} + \mu \sum_{i\sigma} n_{i\sigma} \quad (4)$$

We introduce the 2×2 composite Green's function matrix at sites i and j , with spins σ and σ' and defined for an imaginary time τ by

$$\mathbf{S}_{ij\sigma\sigma'}^{loc}(\tau, \tau') = \langle\langle \psi_{i\sigma}(\tau); \psi_{j\sigma'}^\dagger(\tau') \rangle\rangle_{loc} \quad (5)$$

Where, for two operators X and Y,

$$\langle\langle X(\tau); Y(\tau') \rangle\rangle_{loc} = \theta_H(\tau - \tau') \langle\{X(\tau); Y(\tau')\}\rangle_{loc} \quad (6)$$

Where $\theta_H(\tau - \tau')$ is one if $\tau > \tau'$ and zero otherwise (Heaviside function). $\langle\dots\rangle_{loc}$ denotes the thermal average taken with the Hamiltonian H_{loc} and $\{X(\tau); Y(\tau')\}$ is the anticommutator of X and Y. Since we are at equilibrium we have $\mathbf{S}_{ij\sigma\sigma'}^{loc}(\tau, \tau') = \mathbf{S}_{ij\sigma\sigma'}^{loc}(\tau - \tau')$. By differentiating with respect to time, we get the following equations of motion for the composite Green's function matrix

$$\begin{aligned} \frac{d}{d\tau} \mathbf{S}_{ij\sigma\sigma'}^{loc}(\tau) &= \delta(\tau) \delta_{\sigma\sigma'} \langle\{\psi_{i\sigma}(\tau); \psi_{j\sigma}^\dagger(0)\}\rangle_{loc} \\ &+ \delta_{\sigma\sigma'} \langle\langle[\psi_{i\sigma}(\tau); H_{loc}]; \psi_{j\sigma}^\dagger(0)\rangle\rangle_{loc} \end{aligned} \quad (7)$$

Where $[A; B]$ is the usual commutator between two operators A and B. We enforce a paramagnetic solution by adding $\delta_{\sigma\sigma'}$ prefactor. The currents in the atomic limit are given by

$$J_{i\sigma}^{loc}(\tau) = \frac{d}{d\tau} \psi_{i\sigma}(\tau) = [\psi_{i\sigma}(\tau); H_{loc}] = \mathbf{A} \psi_{i\sigma}(\tau) \quad (8)$$

With

$$\mathbf{A} = \begin{pmatrix} \mu & 0 \\ 0 & U - \mu \end{pmatrix} \quad (9)$$

The equations of motion becomes

$$\begin{aligned} \frac{d}{d\tau} \mathbf{S}_{ij\sigma\sigma'}^{loc}(\tau) &= \\ \delta(\tau) \delta_{\sigma\sigma'} \langle\{\psi_{i\sigma}(\tau); \psi_{j\sigma}^\dagger(0)\}\rangle_{loc} &- \mathbf{A} \mathbf{S}_{ij\sigma\sigma'}^{loc}(\tau) \end{aligned} \quad (10)$$

By time fourier transform we get

$$\mathbf{S}_{ij\sigma\sigma'}^{loc}(\omega) = \delta_{\sigma\sigma'} (\omega - \mathbf{A} + i0^+)^{-1} \mathbf{I}_{i\sigma}^{loc} \delta_{ij} \quad (11)$$

With $\mathbf{I}_{i\sigma}^{loc} = \langle\{\psi_{i\sigma}; \psi_{i\sigma}^\dagger\}\rangle_{loc}$ the normalization matrix and 0^+ a small positive parameter used for analytic continuation since we are working with Matsubara time τ . This matrix can be explicitly computed. A bit of algebra leads to

$$\mathbf{I}_{i\sigma}^{loc} = \begin{pmatrix} 1 - \langle n_{i\sigma} \rangle_{loc} & 0 \\ 0 & \langle n_{i\sigma} \rangle_{loc} \end{pmatrix} \quad (12)$$

We finally obtain

$$\mathbf{S}_{ij\sigma\sigma'}^{loc}(\omega) = \delta_{ij} \delta_{\sigma\sigma'} \begin{pmatrix} 1 - \frac{\langle n_{i\sigma} \rangle_{loc}}{\omega - \mu + i0^+} & 0 \\ 0 & \frac{\langle n_{i\sigma} \rangle_{loc}}{\omega - U + \mu + i0^+} \end{pmatrix} \quad (13)$$

In the atomic limit the equations of motion can therefore be closed. The solution is given in Eq. (11), and by using the relation between composite and electronic operators $\xi_{i\sigma} + \eta_{i\sigma} = c_{i\sigma}$, we can deduce the electronic Green's function

$$\begin{aligned} G_{ij\sigma\sigma'}^{loc}(\tau) &= \delta_{\sigma\sigma'} \langle\langle c_{i\sigma}(\tau); c_{j\sigma'}^\dagger \rangle\rangle_{loc} \\ &= \delta_{\sigma\sigma'} (S_{ij\sigma}^{11\ loc}(\tau) + S_{ij\sigma}^{12\ loc}(\tau) \\ &+ S_{ij\sigma}^{21\ loc}(\tau) + S_{ij\sigma}^{22\ loc}(\tau)) \end{aligned} \quad (14)$$

Where $S_{ij\sigma}^{nm\ loc} = \langle\langle \psi_{i\sigma}^n(\tau); \psi_{j\sigma}^m(0) \rangle\rangle_{loc}$. Therefore we have showed that the composite operators we introduced solve exactly the atomic limit. The electronic Green's function can be directly recovered, allowing to extract all of the information we want from the system.

2. General case

Let us consider the full Hamiltonian Eq. (1) that includes both the local term H_{loc} and the hopping term t . We consider the limit $U \gg t$ and we build an approximation from the atomic limit. From now on, $\langle\dots\rangle$ are the thermal averages taken with the full Hamiltonian. We then introduce

$$\delta J_{i\sigma} = [\psi_{i\sigma}, H - H_{loc}] = J_{i\sigma} - J_{i\sigma}^{loc} \quad (15)$$

Where the current operator in the atomic limit is given by Eq. (8) and $J_{i\sigma} = [\psi_{i\sigma}, H]$ is the current operator taken with the full Hubbard Hamiltonian Eq. (1). Because of the tight-binding term, higher order Green's functions will appear in the equations of motion of the composite Green's function. We will not be able to solve the problem exactly as in the atomic limit. We thus need to do an approximation to be able to obtain the composite Green's function by truncating the equations of motion. Indeed, let us consider the composite Green's functions 2×2 matrix $\mathbf{S}_{ij\sigma\sigma'}(\tau) = \delta_{\sigma\sigma'} \langle\langle \psi_{i\sigma}(\tau); \psi_{j\sigma'}(0) \rangle\rangle$ with thermal average on the full Hamiltonian. Its equations of motion can be written as

$$\frac{d}{d\tau} \mathbf{S}_{ij\sigma\sigma'}(\tau) = \delta_{\sigma\sigma'}(\delta(\tau)\delta_{ij}\mathbf{I}_{i\sigma} + \theta_H(\tau)\mathbf{M}_{ij\sigma}(\tau)) \quad (16)$$

Where we introduced the normalization matrix \mathbf{I} and the overlap matrix \mathbf{M} respectively as

$$\begin{aligned} \mathbf{I}_{i\sigma} &= \langle \{\psi_{i\sigma}, \psi_{i\sigma}^\dagger\} \rangle = \delta_{ij} \begin{pmatrix} 1 - \langle n_{i\sigma} \rangle & 0 \\ 0 & \langle n_{i\sigma} \rangle \end{pmatrix} \\ \mathbf{M}_{ij\sigma} &= \langle \{J_{i\sigma}, \psi_{j\sigma}^\dagger\} \rangle = \begin{pmatrix} m_{ij}^{11} & m_{ij}^{12} \\ m_{ij}^{12} & m_{ij}^{22} \end{pmatrix} \end{aligned} \quad (17)$$

To solve the equations of motion for the composite Green's function matrix, we need to compute the \mathbf{I} and \mathbf{M} matrix. We directly computed the \mathbf{I} matrix. Hereafter we focus on the determination of \mathbf{M} . The current of the total Hamiltonian is given by

$$J_{i\sigma} = \sum_l \mathbf{E}_{il\sigma} \psi_{l\sigma} + \delta\phi_{i\sigma} \quad (18)$$

$$\mathbf{E}_{il\sigma} = \mathbf{A}\delta_{il} + \mathbf{P}_{il\sigma} \quad (19)$$

The \mathbf{E} contains all the terms proportional to ψ , and $\delta\phi_{i\sigma}$ contains all terms which are not. The \mathbf{A} matrix appearing in \mathbf{E} is the contribution of the atomic limit terms. It is given by

$$\mathbf{A} = \begin{pmatrix} \mu & 0 \\ 0 & U - \mu \end{pmatrix} \quad (20)$$

The \mathbf{P} matrix appearing in \mathbf{E} is defined by

$$\mathbf{P}_{ij\sigma} = \langle \{\delta J_{i\sigma}; \psi_{j\sigma}^\dagger\} \rangle \mathbf{I}_{j\sigma}^{-1} \quad (21)$$

\mathbf{P} is the contribution of the terms proportional to ψ in $\delta J_{i\sigma}$.

With this rewriting, the \mathbf{M} matrix is now given by the following expression

$$\begin{aligned} \mathbf{M}_{il\sigma}(\tau) &= \sum_j \mathbf{E}_{ij\sigma} \langle \{\psi_{j\sigma}(\tau); \psi_{l\sigma}^\dagger\} \rangle \\ &+ \langle \{\delta\phi_{i\sigma}(\tau); \psi_{l\sigma}^\dagger\} \rangle \end{aligned} \quad (22)$$

The first term is proportional to $\mathbf{S}_{jl\sigma\sigma'}$. However the second term is not and will introduce higher-order Green's function in the equations of motion

$$\begin{aligned} \frac{d}{d\tau} \mathbf{S}_{ij\sigma\sigma'}(\tau) &= \delta_{\sigma\sigma'}(\delta(\tau)\delta_{ij}\mathbf{I}_{i\sigma} + \sum_l \mathbf{E}_{il\sigma} \mathbf{S}_{lj\sigma}(\tau) \\ &+ \theta_H(\tau) \langle \{\delta\phi_{i\sigma}(\tau); \psi_{l\sigma}^\dagger\} \rangle \end{aligned} \quad (23)$$

An approximation is needed: we will assume that $\delta\phi_{i\sigma}$ is negligible. Therefore, we have

$$\mathbf{S}_{ij\sigma\sigma'}(\omega) \approx \delta_{\sigma\sigma'}(\omega - \mathbf{E}_{ij\sigma} + i0^+)^{-1} \mathbf{I}_{j\sigma} \quad (24a)$$

$$J_{i\sigma}(\tau) \approx \sum_l \mathbf{E}_{il\sigma} \psi_{l\sigma}(\tau) \quad (24b)$$

$$\mathbf{E}_{ij\sigma} \approx \mathbf{M}_{ij\sigma}(0) \mathbf{I}_{jj\sigma}^{-1} \quad (24c)$$

Where these three equations are direct consequences from the approximation. The first one is obtained by applying a time Fourier transform on the equation of motion. The second equation is the current from Eq. (19) and the last equation is Eq. (22) at equal imaginary time (notice that $\mathbf{S}_{ij\sigma}(0) = \delta_{ij}\mathbf{I}_{i\sigma}$).

In appendix A, this approximation is studied in depth and we detail the physical consequences of neglecting $\delta\phi$. \mathbf{E} acts as an effective energy matrix. Note that Eq. (24b) is similar to a Schrödinger equation for the composite operators. We can also include higher order terms in the basis to go further in the approximation. This has been done in Ref. [16].

The equations of motion of the composite Green's function only depends on the \mathbf{E} and \mathbf{I} matrices under our approximation. In order to perform a self-consistent scheme, we introduce the 2×2 correlation function matrix

$$\mathbf{C}_{ij\sigma} = \langle \psi_{i\sigma} \psi_{j\sigma}^\dagger \rangle \quad (25)$$

We want to find an expression of $\mathbf{C}_{ij\sigma\sigma'}$ as a function of the eigenvalues of the \mathbf{E} matrix. Using the spectral representation we get

$$\mathbf{C}_{ij\sigma} = \int d\omega (1 - f_D(\omega)) \left(-\frac{1}{\pi} \right) \text{Im}(\mathbf{S}_{ij\sigma}(\omega)) \quad (26)$$

With $f_D = \frac{1}{\text{Exp}(\beta\omega) + 1}$ the Fermi Dirac distribution. From there, we can use Eq. (24a) to apply the residue theorem on \mathbf{S} and express it as a function of the eigenvalues of the \mathbf{E} matrix (proof in appendix B)

$$\mathbf{S}_{ij\sigma}(\omega) = \sum_{a=1}^2 \frac{\kappa_{ij\sigma}^a}{(\omega - \epsilon_{ij\sigma}^a + i0^+)} \quad (27)$$

With

$$\kappa_{ij\sigma}^a = \frac{(-1)^{a+1} \text{Com}(\epsilon_{ij\sigma}^a - \mathbf{E}_{ij\sigma})^T \mathbf{I}_{j\sigma}}{(\epsilon_{ij\sigma}^1 - \epsilon_{ij\sigma}^2)} \quad (28)$$

Where $Com(\mathbf{A}_{ij}) = (-1)^{i+j} det(\mathbf{A}'_{ij})$ is the cofactor matrix of \mathbf{A} , and \mathbf{A}' is the matrix that results from deleting row i and column j of \mathbf{A} . In these equations, $a \in \{1, 2\}$ and ϵ_{ij}^1 , and ϵ_{ij}^2 are the two eigenvalues of the energy matrix $\mathbf{E}_{ij\sigma}$. Finally, combining Eq. (26) and (27) leads to an expression of the correlation function as a function of ϵ^a

$$\mathbf{C}_{ij\sigma} = \frac{1}{2} \left(1 + \tanh \frac{\beta \epsilon_{ij\sigma}^1}{2} \right) \kappa_{ij\sigma}^1 + \frac{1}{2} \left(1 + \tanh \frac{\beta \epsilon_{ij\sigma}^2}{2} \right) \kappa_{ij\sigma}^2 \quad (29)$$

Where $\beta = \frac{1}{k_B T}$ comes from the Fermi Dirac distribution. To summarize, from the \mathbf{M} and \mathbf{I} matrices we can obtain the energy matrix \mathbf{E} . We showed that its eigenvalues are directly related to the composite correlation function $\mathbf{C}_{ij\sigma\sigma}$. To close the system, in the next section we explicitly compute the \mathbf{M} and \mathbf{I} matrices and express them as a function of the correlation functions.

B. Self-consistent scheme

1. Self-consistent equations of the one-body parameters

We can compute the algebra associated to our composite operators defined in Eq. (2). We assume spin rotational symmetric solutions, allowing us to have $\delta_{\sigma\sigma'}$ in our Green's and correlation functions. This implies

$$\langle n_{i\uparrow} \rangle = \langle n_{i\downarrow} \rangle = \frac{n_i}{2} \quad (30)$$

We compute explicitly the currents

$$j_{i\sigma}^1 = -\mu \xi_{i\sigma} - \sum_l t_{il} \left(c_{l\sigma} - n_{i\bar{\sigma}} c_{l\sigma} + S_i^{sign(\bar{\sigma})} c_{l\bar{\sigma}} + sign(\bar{\sigma}) \Delta_i c_{l\bar{\sigma}}^\dagger \right) \\ j_{i\sigma}^2 = -(\mu - U) \eta_{i\sigma} + \sum_l t_{il} \left(-n_{i\bar{\sigma}} c_{l\sigma} + S_i^{sign(\bar{\sigma})} c_{l\bar{\sigma}} + sign(\bar{\sigma}) \Delta_i c_{l\bar{\sigma}}^\dagger \right) \quad (31)$$

With $S_i^- = c_{i\downarrow}^\dagger c_{i\uparrow}$, $S_i^+ = c_{i\uparrow}^\dagger c_{i\downarrow}$ and $\Delta_i = c_{i\uparrow} c_{i\downarrow}$. We take the following convention: $sign(\uparrow) = 1$ and $sign(\downarrow) = -1$.

The coefficients of the \mathbf{M} matrix are (some details

of the algebra can be found in appendix C)

$$m_{ij}^{11} = -\mu \left(1 - \frac{n_i}{2} \right) \delta_{ij} - \delta_{ij} \sum_l t \alpha_{il}^1 e_{il} - t \alpha_{ij}^1 (1 - n_i + p_{ij}) \\ m_{ij}^{12} = \delta_{ij} \sum_l t \alpha_{il}^1 e_{il} - t \alpha_{ij}^1 \left(\frac{n_i}{2} - p_{ij} \right) \\ m_{ij}^{22} = -(\mu - U) \frac{n_i}{2} \delta_{ij} - \delta_{ij} \sum_l t \alpha_{il}^1 e_{il} - t \alpha_{ij}^1 p_{ij} \quad (32)$$

With

$$e_{ij} = \langle \xi_{j\sigma} \xi_{i\sigma}^\dagger \rangle - \langle \eta_{j\sigma} \eta_{i\sigma}^\dagger \rangle \\ p_{ij} = \langle n_{i\sigma} n_{j\sigma} \rangle + \langle S_i^- S_j^+ \rangle - \langle \Delta_i \Delta_j^* \rangle \quad (33)$$

$\alpha_{il}^1 = \frac{t_{il}}{t}$ is equal to 1 if i and l are nearest neighbors, and 0 otherwise.

The parameter e contains correlations between neighboring composite operators and will mainly re-normalize the chemical potential because it always appear in \mathbf{M} in front of a δ_{ij} . The p parameter contains charge-charge, spin-spin and pair-pair correlations and will affect the bandwidth.

We now use the translational invariance of the system: each parameters with a dependence in two sites i and j will only depend on the distance between these two sites $i - j$. Hence we get

$$e_{ij} = e_{i-j} \\ p_{ij} = p_{i-j} \\ \mathbf{M}_{ij} = \mathbf{M}_{i-j} \quad (34)$$

We assume lattice inversion and rotation (C_4) symmetries and we take n , p and e as constants

$$n_i = n \\ p_{i\pm\delta_x} = p_{i\pm\delta_y} = p \\ e_{i\pm\delta_x} = e_{i\pm\delta_y} = e \quad (35)$$

Under these assumptions the coefficients of the \mathbf{M} matrix become

$$m_{ij}^{11} = -\mu \left(1 - \frac{n}{2} \right) \delta_{ij} - \delta_{ij} 4te - t \alpha_{ij}^1 (1 - n + p) \\ m_{ij}^{12} = \delta_{ij} 4te - t \alpha_{ij}^1 \left(\frac{n}{2} - p \right) \\ m_{ij}^{22} = -(\mu - U) \frac{n}{2} \delta_{ij} - \delta_{ij} 4te - t \alpha_{ij}^1 p \quad (36)$$

And the \mathbf{E} matrix defined by Eq. (24c) is given by

$$\mathbf{E}_{ij} = \begin{pmatrix} \frac{2}{2-n}m_{ij}^{11} & \frac{2}{n}m_{ij}^{12} \\ \frac{2}{2-n}m_{ij}^{12} & \frac{2}{n}m_{ij}^{22} \end{pmatrix} \quad (37)$$

This matrix is diagonalizable and Eq. (29) allows to express the correlation function $\mathbf{C}_{ij\sigma} = \langle \psi_{i\sigma} \psi_{j\sigma}^\dagger \rangle$ as a function of its eigenvalues. Thus in order to close the system and be able to solve it self-consistently we need to express the parameters in the \mathbf{M} matrix as a function of the correlation functions. A diagram of the self-consistent loop is given in Fig. 1 for clarity.

Since e and n are one-body parameters, therefore they can directly be expressed as

$$\begin{aligned} n &= 2(1 - C_0^{11} - 2C_0^{12} - C_0^{22}) \\ e &= C_{ij}^{11} - C_{ij}^{22} \end{aligned} \quad (38)$$

In this equation $\mathbf{C}_0 = \mathbf{C}_{ii}$ are constants by translational invariance. and $\mathbf{C} = \mathbf{C}_{ij} = \mathbf{C}_{i-j}$ is treated as e and p in Eq. (35) using lattice inversion and rotation (C_4) symmetry, so it is also a constant but different from \mathbf{C}_0 .

Expressing p as a function of the correlations functions is not so direct since p is composed of two-bodies operators while e , n and C are one-body operators.

2. Self-consistent equations of two-bodies operators : Roth decoupling

Following the step of L. Roth [11], we express p as a function of correlation functions by mean of equations of motion. We give here the main idea of the decoupling, taking the pair-pair term $\langle \Delta_i \Delta_j^* \rangle$ as an example. The full details of the computation can be found in Appendix D. First, notice we can write

$$\langle \Delta_i \Delta_j^* \rangle = \langle \xi_{i\uparrow} c_{i\downarrow} \Delta_j^* \rangle + \langle \eta_{i\uparrow} c_{i\downarrow} \Delta_j^* \rangle \quad (39)$$

Note we illustrate this decoupling with $\xi_{i\uparrow}$ and $\eta_{i\uparrow}$ but the idea is exactly the same with $\psi_{i\downarrow}$. We introduce the following Green's functions

$$\begin{cases} F_{ijl}(\tau) &= \langle \langle \xi_{i\uparrow}(\tau); c_{j\downarrow} \Delta_l^* \rangle \rangle \\ G_{ijl}(\tau) &= \langle \langle \eta_{i\uparrow}(\tau); c_{j\downarrow} \Delta_l^* \rangle \rangle \end{cases} \quad (40)$$

We then consider the equations of motion for these Green's functions

$$\begin{aligned} \partial_\tau \begin{pmatrix} F_{ijl}(\tau) \\ G_{ijl}(\tau) \end{pmatrix} &= \theta_H(\tau) \begin{pmatrix} \langle \langle \partial_t \xi_{i\uparrow}(\tau); c_{j\downarrow} \Delta_l^* \rangle \rangle \\ \langle \langle \partial_\tau \eta_{i\uparrow}(\tau); c_{j\downarrow} \Delta_l^* \rangle \rangle \end{pmatrix} \\ &+ \delta(\tau) \begin{pmatrix} f_{ijl}^1 \\ f_{ijl}^2 \end{pmatrix} \end{aligned} \quad (41)$$

where $f_{ijl}^n = \langle \langle \psi_i^n; c_{j\downarrow} \Delta_k^* \rangle \rangle$. We now use Eq. (24b) to obtain

$$\partial_\tau \begin{pmatrix} F_{ijl}(\tau) \\ G_{ijl}(\tau) \end{pmatrix} = \sum_k E_{ik} \begin{pmatrix} F_{kjl}(\tau) \\ G_{kjl}(\tau) \end{pmatrix} + \delta(\tau) \begin{pmatrix} f_{ijl}^1 \\ f_{ijl}^2 \end{pmatrix} \quad (42)$$

We then time Fourier transform and use Eq. (24a) to obtain

$$\begin{pmatrix} F_{ijl}(\omega) \\ G_{ijl}(\omega) \end{pmatrix} = \sum_k S_{ik}(\omega) I^{-1} \begin{pmatrix} f_{kjl}^1 \\ f_{kjl}^2 \end{pmatrix} \quad (43)$$

Finally, we can extract $\langle \Delta_i \Delta_j^* \rangle$ by summing F and G , integrating over ω and taking the imaginary part to use Eq. (26) in order to replace the composite Green's functions by correlation functions. We get

$$\begin{aligned} \langle c_{i\sigma} c_{j\bar{\sigma}} \Delta_l^* \rangle &= \frac{2}{2-n} \sum_k (C_{ik}^{11} + C_{ik}^{12}) f_{kjl}^1 \\ &+ \frac{2}{n} \sum_k (C_{ik}^{12} + C_{ik}^{22}) f_{kjl}^2 \end{aligned} \quad (44)$$

The computation of $f_{kjl}^n = \langle \langle \psi_k^n; c_{j\downarrow} \Delta_l^* \rangle \rangle$ is done in appendix D. Setting $i = j$, we finally get

$$\langle \Delta_i \Delta_l^* \rangle = \frac{4}{n(2-n)} \frac{(C_{il}^{11} + C_{il}^{12})(C_{il}^{22} + C_{il}^{21})}{1 - \frac{2}{2-n}(C_0^{11} + C_0^{12}) + \frac{2}{n}(C_0^{21} + C_0^{22})} \quad (45)$$

The same method can be applied for $\langle n_{i\sigma} n_{l\sigma} \rangle$ and $\langle S_i^+ S_l^- \rangle$, the details are in appendix D. Note that we always obtain numerically $C_0^{21} = C_0^{12}$. Finally, the expressions for the parameters appearing in \mathbf{M} and \mathbf{I} as a function of the $C_{ij}^{nm} = \langle \psi_i^n (\psi_j^m)^\dagger \rangle$ are the following

$$\begin{cases} e &= C^{11} - C^{22} \\ n &= 2(1 - C_0^{11} - 2C_0^{12} - C_0^{22}) \\ p &= \frac{n^2}{4} - \frac{\rho_1}{1-\phi^2} - \frac{\rho_1}{1-\phi} - \frac{\rho_3}{1+\phi} \end{cases} \quad (46)$$

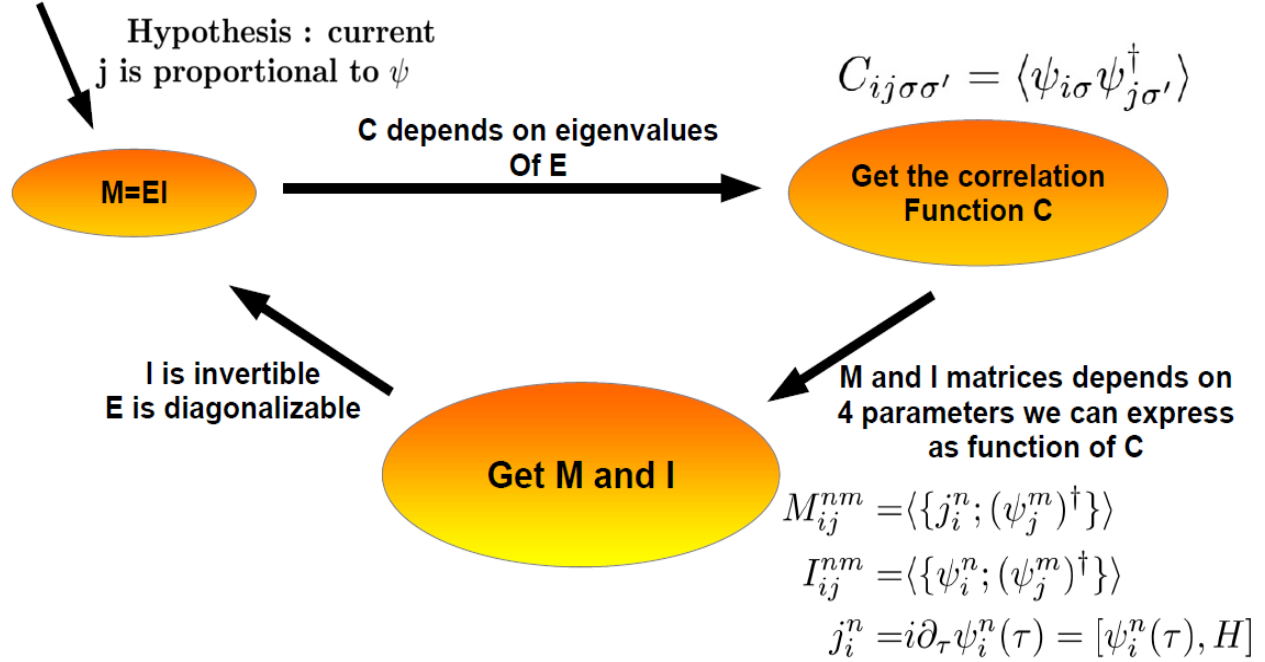


Figure 1: The self consistency loop. Our hypothesis on the currents allows us to get a relation between the \mathbf{M} and \mathbf{I} matrices (Eq. (24c)). The energy matrix \mathbf{E} is diagonalizable. We can express correlation functions as a function of its eigenvalues with Eq. (29). Then, we can rewrite the \mathbf{M} and \mathbf{I} matrices in term of these correlations functions and do a self-consistency (Eq. (46)).

With

$$\begin{cases} \phi &= \frac{2}{2-n}(C_0^{11} + C_0^{12}) + \frac{2}{n}(C_0^{12} + C_0^{22}) \\ \rho_1 &= \frac{2}{2-n}(C^{11} + C^{12})^2 + \frac{2}{n}(C^{22} + C^{12})^2 \\ \rho_3 &= \frac{4}{n(2-n)}(C^{11} + C^{12})(C^{22} + C^{12}) \end{cases} \quad (47)$$

With the self consistent equations Eq. (46) on the parameters n , e and p we just closed the system. In Fig. 1, we represented the self-consistency pattern. Starting from initial guess for e , n and p , we compute the \mathbf{M} and \mathbf{I} matrices. We can then obtain \mathbf{E} and diagonalize it. Then, using Eq. (29), we can express the correlation functions from its eigenvalues. Finally, using the self consistent Eq. (46), we compute again e , p and n . We stop when $f(x) - x < \delta$ where $x = (e, p, \mu)$ and f are given in Eq. (46). We chose $\delta = 10^{-8}$. Once the system converges, we use the parameters (e, p, μ) to compute the electronic Green's function

$$\begin{aligned} G_{ij}(\omega) &= S_{ij}^{11}(\omega) + S_{ij}^{12}(\omega) + S_{ij}^{21}(\omega) + S_{ij}^{22}(\omega) \\ &= \sum_{l=1}^2 \frac{(\kappa^l)_{ij}^{11} + (\kappa^l)_{ij}^{12} + (\kappa^l)_{ij}^{21} + (\kappa^l)_{ij}^{22}}{\omega - \epsilon_{ij}^l + i0^+} \end{aligned} \quad (48)$$

Where the κ act as spectral weights and are defined in Eq. (28) and $\epsilon^{1/2}$ are the eigenvalues of the \mathbf{E} matrix, and can be built from the parameters (e, p, μ) .

III. NEAREST-NEIGHBOUR STUDY

This self-consistent scheme has a drawback. With the numerical solution of the self consistent equations we obtain a non vanishing C_0^{12} . However, analytically this correlation function is zero because of the Pauli principle.

$$\begin{aligned} C_0^{12} &= \langle \xi_{i\sigma} \eta_{i\sigma}^\dagger \rangle \\ &= \langle (c_{i\sigma} - c_{i\sigma} n_{i\bar{\sigma}}) c_{i\sigma}^\dagger n_{i\bar{\sigma}} \rangle \\ &= \langle c_{i\sigma} c_{i\sigma}^\dagger n_{i\bar{\sigma}} + c_{i\sigma} c_{i\bar{\sigma}}^\dagger c_{i\sigma}^\dagger c_{i\bar{\sigma}} n_{i\bar{\sigma}} \rangle \\ &= \langle -c_{i\sigma} (c_{i\bar{\sigma}}^\dagger)^2 c_{i\bar{\sigma}}^\dagger (c_{i\bar{\sigma}})^2 \rangle \\ &= 0 \end{aligned} \quad (49)$$

This numerical violation of the Pauli principle gets smaller as U becomes larger than t [9].

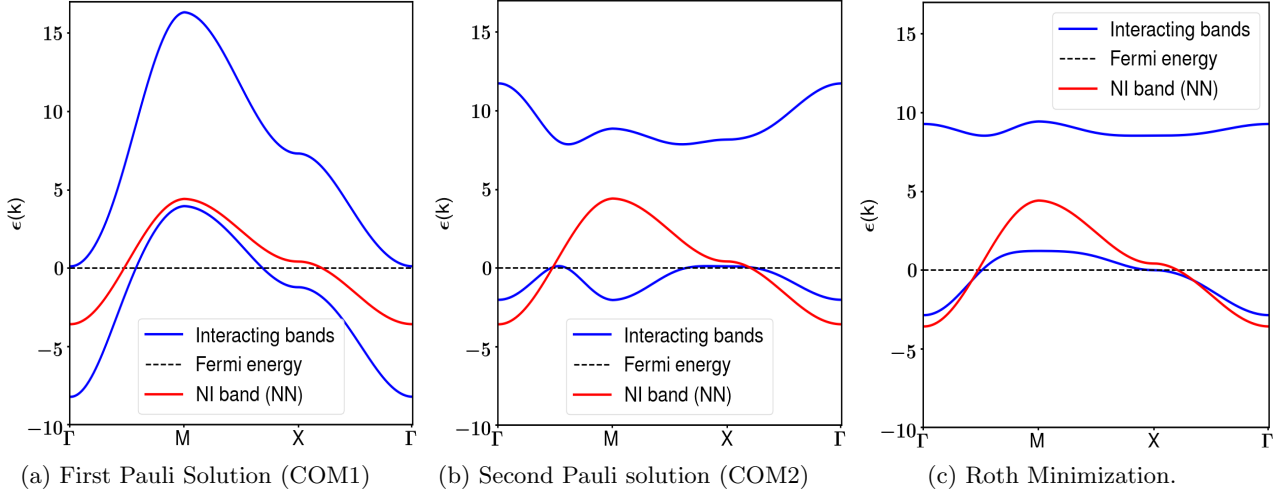


Figure 2: Bands along high symmetry points with $t = 1, U = 8t, T = 0, n = 0.8$. The non interacting (NI) band (red line) is splitted in 2 Hubbard bands obtained for every solutions with the composite operator method (blue lines). Therefore at half filling the chemical potential lies in between the two Hubbard bands and we get a Mott insulator. (a) One of the two solutions obtained with Pauli minimization (using Eq. (49) instead of the p parameter in Eq. (46)). It has no renormalization from the interaction since the shape of the Hubbard bands is similar to the non-interacting band. (b) The second solution obtained with the Pauli minimization. It has a minimum at $M=(\pi, \pi)$ and exhibits two hole pockets. (c) The solution obtained with the Roth minimization. We observe a flattening of the bands around $X=(\pi, 0)$.

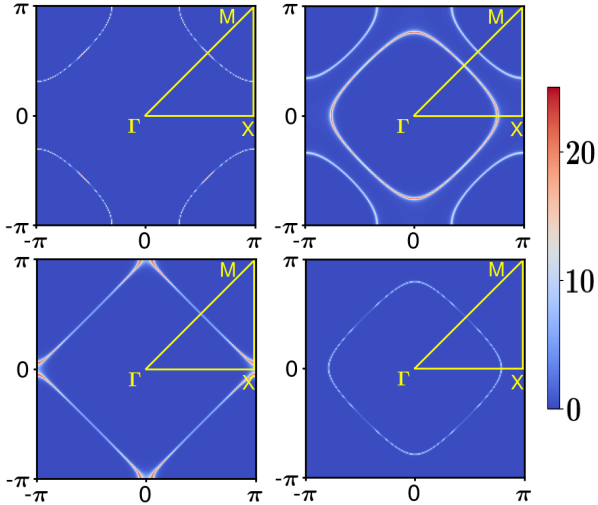


Figure 3: Fermi Surfaces obtained from the spectral function (imaginary part of Eq. (48)) at $\omega = 0$, associated to the bands depicted in (2). The parameters are $t = 1, n = 0.8, U = 8t$ and $T = 0$. top left: COM1, top right: COM2, bottom left: Roth, bottom right: Non interacting (tight binding)

It is possible to solve a different set of self-consistent equations by imposing $C_0^{12} = 0$ [16] as the third self consistent equation instead of p in Eq. (46). From now on, we will call the minimization with p the “Roth minimization” since it uses the decoupling formalized by L. Roth and the minimization with C_0^{12} the “Pauli minimization”.

In the following section we consider both minimizations and discuss the bands and Fermi surfaces obtained for each solution we found. We compare to the non interacting tight-binding model, and study the particle-hole symmetry, the Luttinger theorem as well as superconductivity.

A. Comparison of Pauli and Roth minimization

By varying the initial conditions and using a minimizer we isolate two distinct solutions with the Pauli minimization, and one unique solution with the Roth minimization. Following notations from Ref [9], we call these three solutions respectively COM1, COM2 and Roth solutions. In Fig. 2 we plot the bands along high symmetry points for these solutions.

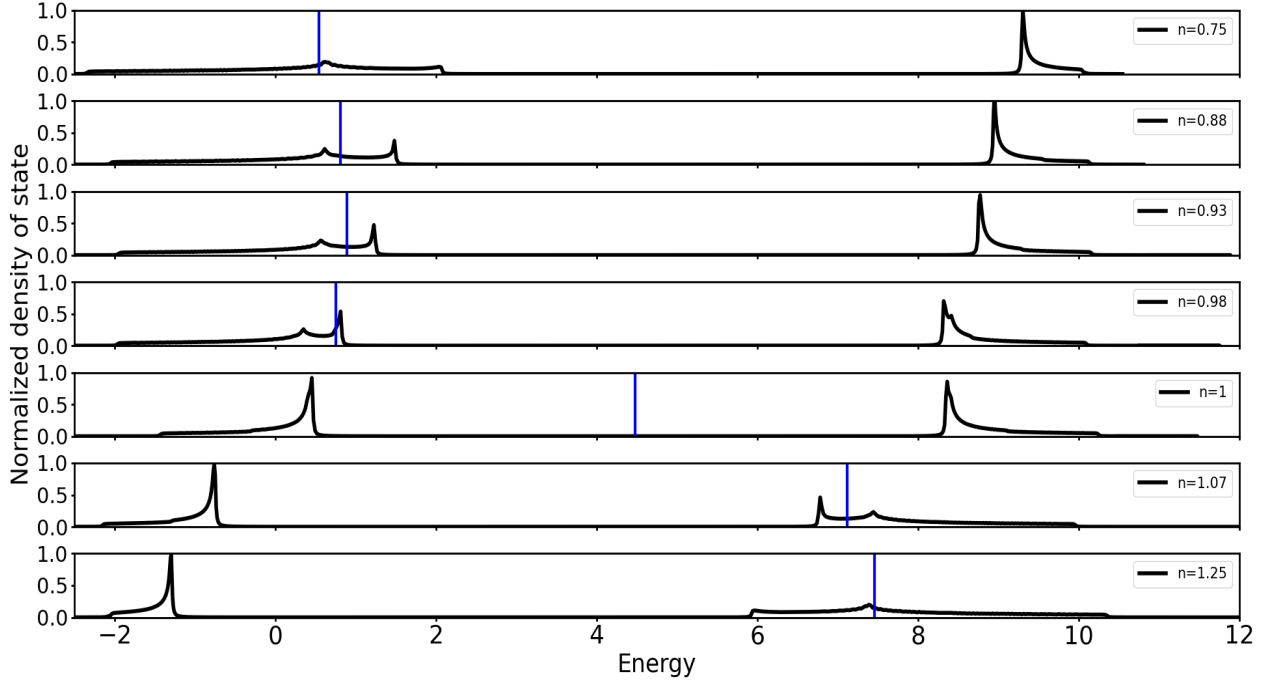


Figure 4: Density of state in energy with parameters $t = 1, U = 8t$ and $T = 0$, using Roth minimization with nearest neighbors. From top to bottom the filling is respectively: $n=0.75, 0.88, 0.93, 0.98, 1$ (half filling), 1.07 and 1.25 . The blue line on each panel corresponds to the chemical potential.

These bands correspond to the eigenvalues of the E matrix and act as the poles of the electronic Green's function (cf Eq. (48)). All of these solutions have two bands associated to the two eigenvalues of the energy matrix, which are splitted by U . COM2 and Roth solution lead to a Mott insulator physics at half-filling because the chemical potential lies in between the two bands. This is not the case for COM1 which is not in an insulating phase at half-filling for $t=1, U=8t$. The bands obtained by COM1 in figure 2a look exactly like the non interacting (NI) tight-binding band for a square lattice $\epsilon_{tb} = 2t(\cos(k_x) + \cos(k_y))$ (the red line), but splitted by U . Therefore this solution is not really normalized by the interaction. COM2 is changed a lot compared to the non interacting case (Fig. 2b), but always presents two holes pockets, leading to two Fermi Surfaces in Fig. 3. This is unexpected, as this has never been observed by ARPES experiments for strongly correlated materials such as cuprates where this treatment of the Hubbard model is relevant. However, in Ref. [16] the basis has been extended to take into account dynamical corrections of the self-

energy (cf appendix A for details). The lifetime of the second hole pocket is then computed and happens to be small, which can explain why it is not observed experimentally. Finally, the Roth solution (Fig. 2c) has a very different shape from the non interactive solution. It also has the advantages of presenting only one hole pocket and a maximum at (π, π) .

Note we plotted the bands we obtained at half filling for the Roth solution in appendix E, on Fig. 17. Close to half filling (around 3% hole doping), the Roth solution exhibits a second small hole pocket at (π, π) (In appendix E we plot the bands and Fermi Surface of Roth decoupling at 2% hole doping in Fig. 16). This second hole pocket around (π, π) may be the consequence of our paramagnetic assumption $\langle n_{i\uparrow} \rangle = \langle n_{i\downarrow} \rangle = \frac{n}{2}$. It appears around half filling where we know the antiferromagnetic phase dominates [17]. The wave-vector (π, π) is also associated with antiferromagnetism, so this second hole pocket might be an instability of the system because we neglected it.

For comparison, in the Hubbard I approximation

(the first and simplest approximation developed by Hubbard in Ref. [8]) a simple factorization procedure of the 2-bodies Green functions is used. According to Ref. [9], Hubbard I approximation in the composite operator framework would be equivalent to set

$$\begin{aligned} e &= 0 \\ p &= \frac{n^2}{4} \end{aligned} \quad (50)$$

It is known that the Hubbard I approximation does not exhibit any Mott-insulator transition as long as $U \neq 0$ (cf Ref. [8]). Therefore the composite operator method is a more refined approximation as Hubbard I.

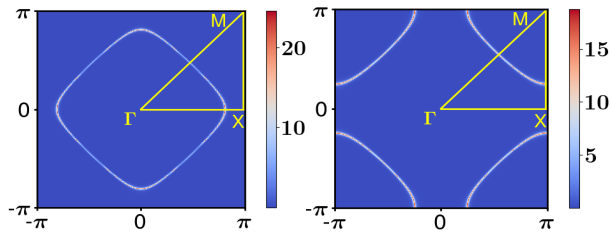


Figure 5: Fermi Surface obtained with Roth solution, at $n=0.7$ and $n=0.9$. The Van Hove singularity is at a chemical potential associated to electron density $n=0.8$. Below the singularity the Fermi surface is centered around $(0, 0)$, and above the singularity it is centered around (π, π)

It is also instructive to consider the density of states. In Fig. 4, we plot it as a function of energy for several doping with the Roth solution. Only Roth solution is considered because it is the one who has the most reasonable Fermi Surface, but similar behaviors are expected for COM1 and COM2. The density of state has been computed from the spectral function using the following formula

$$\mathcal{D}(\omega) = \frac{1}{N_k^2} \sum_{k_x, k_y=1}^{N_k} \left(-\frac{1}{2\pi} \right) \text{Im}(G(\mathbf{k}, \omega)) \quad (51)$$

Where N_k denotes the number of considered points for sampling k_x and k_y . At half filling we do not have any state at the Fermi energy, since the model leads to an insulator for this doping. Around the gap two peaks can be distinguished. For every doping except half filling, a third peak is observable, and corresponds to the Van Hove singularity. It is associated to a flattening of the band, meaning there are

a lot of states associated to this energy. In term of Fermi surface for a square lattice the Van Hove singularity corresponds to the doping below which the Fermi Surface is centered on $(0, 0)$ and above which it is centered on (π, π) , as shown in Fig. 5. On Fig. 2, this flatness of the bands can be found for every solutions around $(\pi, 0)$. The Fermi energy is exactly at the Van Hove singularity for the Roth solution at $n=0.8$ or $n=1.2$. On Fig. 2, the Roth solution is plotted exactly at this doping and we can check the flat band around $(\pi, 0)$ lies exactly at the Fermi energy (corresponding to the dotted black line).

Regarding the Mott transition, we see at half filling no quasiparticle peak is observed around the Fermi energy. Instead, the density of state is closer to what was observed with determinantal quantum Monte Carlo simulation (DQMC) in Ref. [18]. DQMC is a stochastic algorithm which allows under some limitations to perform direct studies of complex condensed matter problems. As predicted by DQMC in Ref [18], at high doping we have only one peak corresponding to a Van Hove singularity (Fermi liquid behavior), and when approaching the Mott transition a transfer of spectral weight occurs, changing the density of states, without creating a quasiparticle peak at the Fermi energy at half filling. Therefore in this regime where $U \gg t$ the density of states of the lower and upper Hubbard bands are the only contribution.

B. Particle-hole symmetry and Luttinger theorem

1. Particle-hole symmetry

It is well known that the Hubbard model with nearest neighbour hoppings only is particle-hole symmetric. This symmetry exchanges particles and holes with the transformation

$$c_{i\sigma} \rightarrow (-1)^i c_{i\sigma}^\dagger \quad c_{i\sigma}^\dagger \rightarrow (-1)^i c_{i\sigma} \quad (52)$$

We could also have taken another convention for this transformation without any $(-1)^i$, as long as we change t to $-t$ to keep the Hamiltonian invariant. Applied to the composite operators one can show that it becomes

$$\eta_{i\sigma} \rightarrow (-1)^i \xi_{i\sigma}^\dagger \quad \xi_{i\sigma} \rightarrow (-1)^i \eta_{i\sigma}^\dagger \quad (53)$$

Let us study the behaviour of the parameters μ , p and e under the particle-hole symmetry. With the

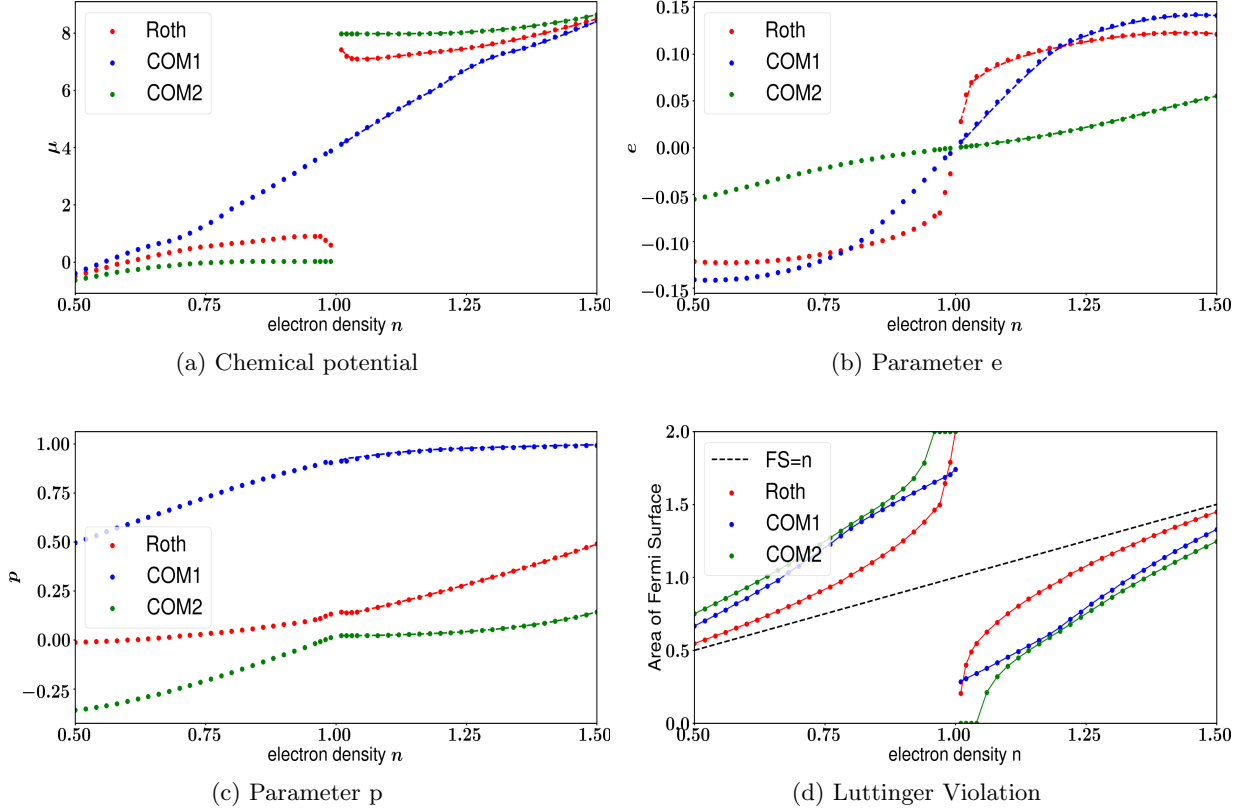


Figure 6: (a), (b) and (c): parameters as a function of doping for each solution. The dash lines in the electron dope ($n > 1$) region are the particle-hole symmetric (55) of their equivalent in the hole doped region. Bottom right: area of Fermi surface as a function of doping. It is computed with the use of Eq. (58). We observe a violation of Luttinger theorem for all solutions. All of these figures are obtained at $T = 0\text{K}$ ($\beta \approx 10^5 t$) and $U = 8t$.

paramagnetic assumption, the particle-hole transformation is rewritten

$$\begin{aligned} \langle c_{i\sigma}^\dagger c_{i\sigma} \rangle &\rightarrow \langle c_{i\sigma} c_{i\sigma}^\dagger \rangle \\ \Leftrightarrow \frac{n}{2} &\rightarrow 1 - \frac{n}{2} \end{aligned} \quad (54)$$

Hence applying the particle-hole transformation on electronic filling gives $n \rightarrow 2-n$. The transformation changes p and e (Eq. (33)) as follow (details are given in appendix G)

$$\begin{aligned} e(2-n) &= -e(n) \\ p(2-n) &= p(n) + (1-n) \\ \mu(2-n) &= U - \mu(n) \end{aligned} \quad (55)$$

The relation of the chemical potential can be obtained by using the fact that the Hubbard Hamil-

tonian must stay invariant under this symmetry for nearest-neighbour hoppings. Finally, applying this transformation on the composite bands ϵ^1 and ϵ^2 leads to

$$\begin{aligned} \epsilon^1(2-n, \mathbf{k}) &= -\epsilon^2(n, \mathbf{k} + (\pi, \pi)) \\ \epsilon^2(2-n, \mathbf{k}) &= -\epsilon^1(n, \mathbf{k} + (\pi, \pi)) \end{aligned} \quad (56)$$

In Fig. 6a, 6b and 6c we plot e , p and μ as a function of doping for the three solutions we studied (COM1, COM2 and Roth). The dashed-lines on the electron-doped region is the value the parameter must have to satisfy the particle-hole relations Eq. (55). We see that particle-hole symmetry is respected for every parameters for the three solutions. The chemical potential presents a jump of the order of U at half filling for the COM2 and Roth solutions.

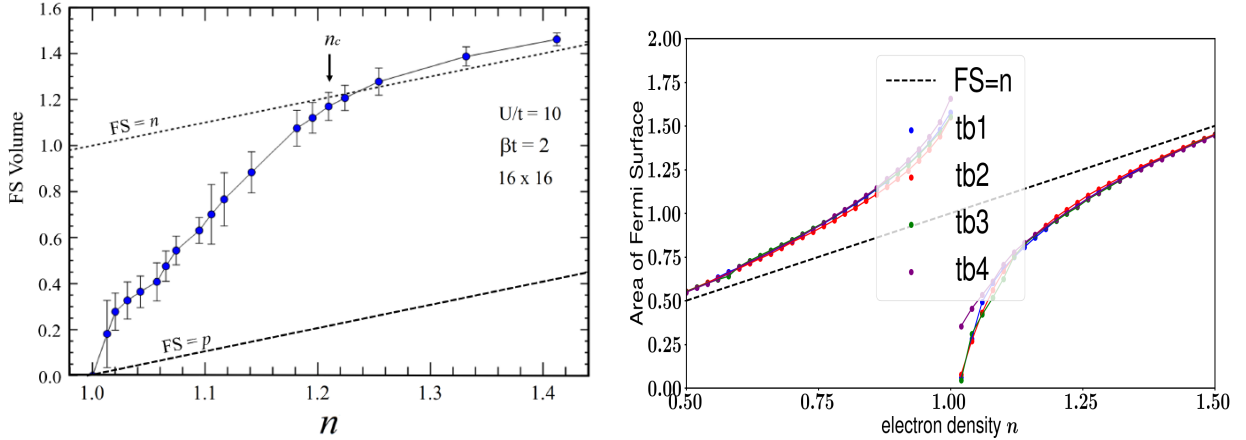


Figure 7: Luttinger violation as a function of electron density. (left): Figure from Ref. [18], obtained from Determinantal Monte Carlo, with $\beta = 2t$ and $U=10t$. (right): Figure we obtain with the method at the same parameters for the three solutions. n_c corresponds to the electron density under which the Luttinger theorem is violated. Above n_c the Fermi surface volume is proportional to the electron density (the curves and the line “FS=n” are parallel). Under n_c this isn’t true anymore and we enter in a “Luttinger breaking phase”.

This is because the lower Hubbard band is filled and the upper Hubbard band starts to be occupied at half filling. COM1 does not exhibit this feature.

We obtain a different result from Ref. [9]. It is possible to have a particle-hole symmetric solution which violates Pauli principle. This is indeed the case of the Roth solution which has a non vanishing C_0^{12} despite the fact it is zero analytically. The solution is particle-hole symmetric as long as C_0^{12} is not put to zero by hand in the self-consistent equations it must appear both in the equation of n and in the ϕ term in the equation of p .

2. Luttinger theorem

We now turn our attention to the Luttinger theorem. This theorem states that the volume enclosed by the Fermi surface is proportional to the electron density [19]. The Luttinger theorem is only demonstrated for systems where the interaction can be treated perturbatively. For this reason it is common that it can be violated in strongly correlated systems. To compute the volume enclosed by the Fermi surface, we need to remember the relation between the composite and electronic Green’s function Eq. (48) The κ act as spectral weights of the elec-

tronic Green’s function. The Fermi surface is given by the imaginary part of this electronic Green’s function at the Fermi energy

$$\begin{aligned}
 A_{ij}(\omega = 0) &= -\frac{1}{\pi} \text{Im}(G_{ij}(\omega = 0)) \\
 &= \frac{1}{\pi} \sum_l \frac{0^+((\kappa^l)_{ij}^{11} + (\kappa^l)_{ij}^{12} + (\kappa^l)_{ij}^{21} + (\kappa^l)_{ij}^{22})}{(\epsilon_{ij}^l)^2 + (0^+)^2}
 \end{aligned} \tag{57}$$

Thus, the Fermi contour is the set of points associated to a vanishing ϵ_{ij}^l . Therefore a way to compute the enclosed area A_{FS} is simply by considering the following equation

$$A_{FS}^l = \frac{1}{N^2} \sum_{k_x, k_y=1}^N \theta_H(\epsilon^l(\mathbf{k})) \tag{58}$$

Note in this last equation we do not have the sum over the two eigenvalues. Indeed, if hole doped, the upper Hubbard band $\epsilon^2(\mathbf{k})$ is never negative so the heaviside function returns zero. In the electron doped regime, the lower Hubbard band is always filled, so it does not affect the Fermi surface. Therefore, if hole doped we take $l=1$, and if electron doped we take $l=2$. Fig. 6d reveals that the Luttinger theorem is violated. This violation is analogous to what

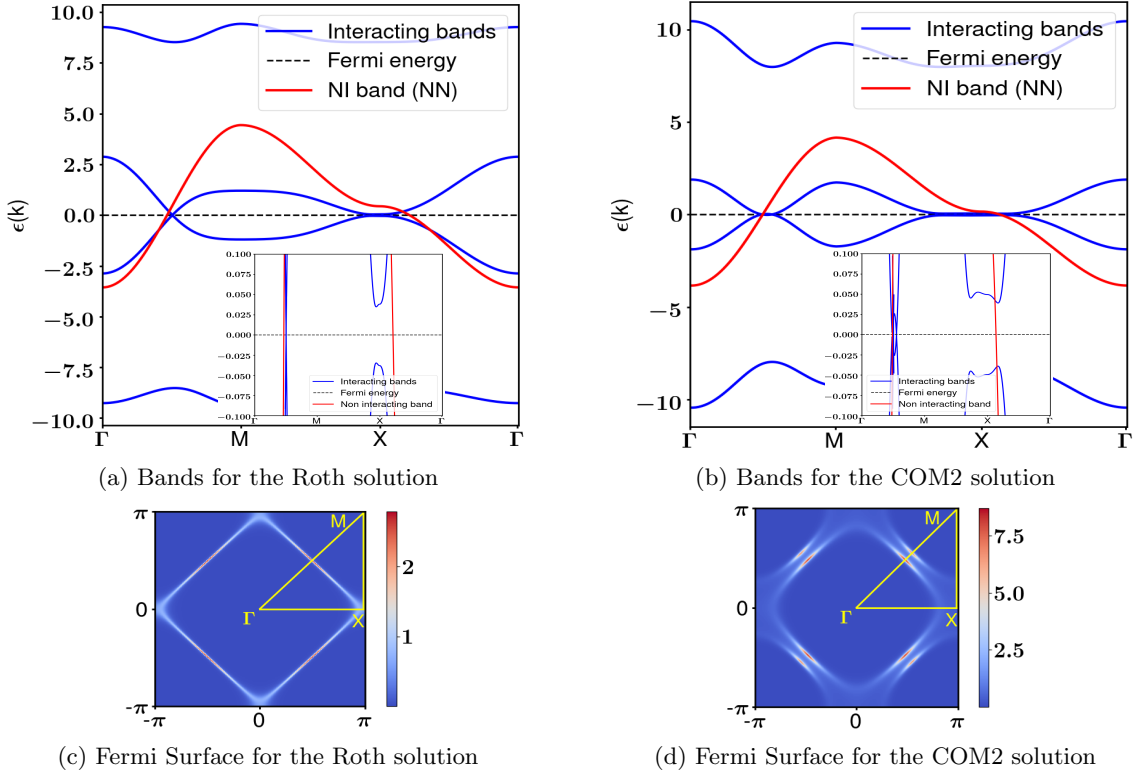


Figure 8: Bands and Fermi Surface with superconductivity at $t = 1$, $U = 8t$ and $T = 0$. The plots on the left correspond to the Roth solution at $n = 0.8$, whereas the plot on the right correspond to COM2 at $n = 0.9$. These are the respective doping at which superconductivity is maximum. We observe a doubling of the bands associated to the doubling of the basis. The insets on the top plots correspond to a zoom around zero energy of the bands: we see a gap opening at $\mathbf{k}=(\pi, 0)$. There is no gap opening between $\mathbf{k}=(0, 0)$ and $\mathbf{k}=(\pi, \pi)$ because of d-wave symmetry. Both Fermi surfaces on the bottom plots have a loss of spectral weight around $\mathbf{k}=(\pi, 0)$.

was observed by Ref. [18] using determinantal quantum Monte-Carlo simulations. In Fig. 7, we plot side by side Luttinger violation taken from this reference and the Luttinger violation we observed with the same parameters ($U=10t$ and $\beta=2$). While none of the solutions we considered are exactly similar to what was observed with determinantal quantum Monte-Carlo, we have the same behavior and conclusion : above a critical electron density n_c , Luttinger theorem is verified and all the solutions are proportional to the electron density (the curves are parallel to the black dashed line). Under n_c this is not the case anymore, we are in a “Luttinger breaking phase”. This is explained in Ref. [18] as a topological order which is a consequence of the proximity to the Mott transition.

C. Superconductivity and Van Hove singularity

1. Method

Superconductivity can be studied by extending the initial basis. The new spinor ψ to consider is

$$\psi = \begin{pmatrix} \xi_{i\sigma} \\ \eta_{i\sigma} \\ \xi_{i\bar{\sigma}}^\dagger \\ \eta_{i\bar{\sigma}}^\dagger \end{pmatrix} \quad (59)$$

The method described before remains the same except for the \mathbf{I} and \mathbf{M} matrix which are now 4×4 matrices. Since we are interested in cuprates, we

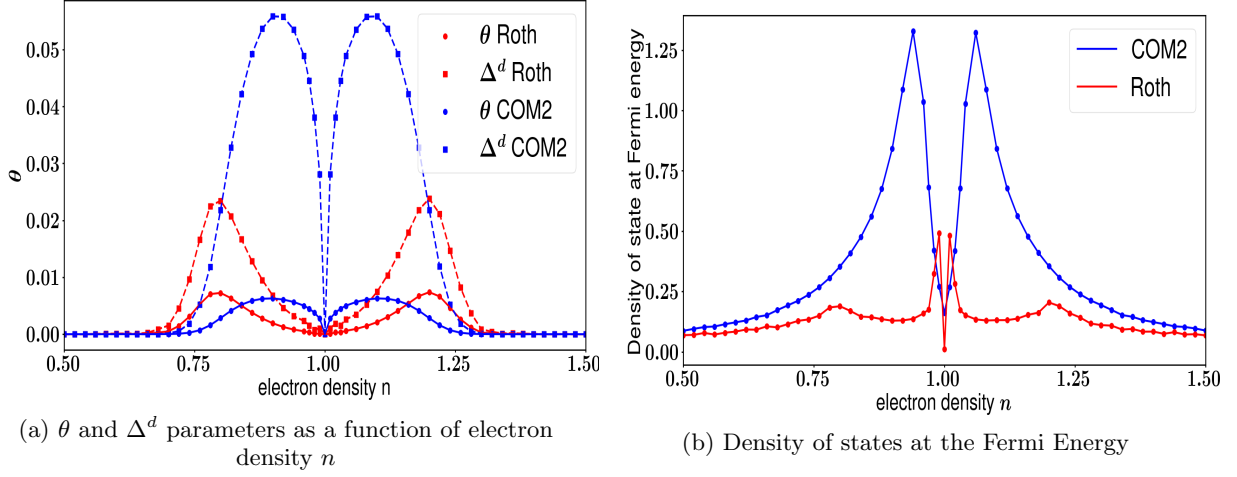


Figure 9: (a): Anomalous superconducting mean field parameter θ as a function of doping for Roth minimization and Pauli minimization (COM2 solution). θ satisfy particle-hole symmetry in both cases. The dashed lines corresponds to the d-wave superconducting order parameter Δ^d . (b): Density of states at the Fermi energy with no superconductivity. We see a clear correlation between enhancement of the density of states and superconductivity. θ and Δ^d are maximum at the Van Hove singularity. It lies at $n=0.8$ for Roth and around $n=0.9$ for COM2, as shown in Fig. 8.

consider only the case of d-wave superconductivity. Therefore, $\langle c_{i\uparrow}c_{i\downarrow} \rangle = 0$. In this framework, the \mathbf{M} and \mathbf{I} matrices are given by

$$\mathbf{I}_i = \begin{pmatrix} 1 - \frac{n_i}{2} & 0 & 0 & 0 \\ 0 & \frac{n_i}{2} & 0 & 0 \\ 0 & 0 & 1 - \frac{n_i}{2} & 0 \\ 0 & 0 & 0 & \frac{n_i}{2} \end{pmatrix} \quad (60)$$

$$\mathbf{M}_{ij} = \begin{pmatrix} m_{ij}^{11} & m_{ij}^{12} & m_{ij}^{13} & -m_{ij}^{13} \\ m_{ij}^{12} & m_{ij}^{22} & -m_{ij}^{13} & m_{ij}^{13} \\ m_{ij}^{13} & -m_{ij}^{13} & -m_{ij}^{11} & -m_{ij}^{12} \\ -m_{ij}^{13} & m_{ij}^{13} & -m_{ij}^{12} & -m_{ij}^{22} \end{pmatrix} \quad (61)$$

The expression of m_{ij}^{11} , m_{ij}^{12} and m_{ij}^{22} are the same as before (cf Eq. (32)). The off diagonal coefficient is given by

$$m_{ij}^{13} = -t\gamma_{ij}\theta_{ij} \quad (62)$$

Where γ_{ij} is a d-wave coefficient such that $\gamma_{i,i\pm\delta_y} = -\gamma_{i\pm\delta_x,i} = 1$ and δ_x/δ_y is the lattice constant along x/y axis. The parameter θ is given by

$$\theta_{ij} = \langle c_{i\sigma}c_{i\bar{\sigma}}n_{j\sigma} \rangle \quad (63)$$

θ_{ij} can be expressed in several symmetry channels. For the sake of giving an intuition of this, we apply Wick theorem on θ_{ij} (this cannot be done since Wick theorem is only valid for weak correlations but it will give an insight of the physics)

$$\begin{aligned} \theta_{ij} = & \langle c_{i\sigma}c_{i\bar{\sigma}} \rangle n_{j\sigma} - \langle c_{i\sigma}c_{j\sigma}^\dagger \rangle c_{i\bar{\sigma}}c_{j\sigma} \\ & + \langle c_{i\sigma}c_{j\sigma} \rangle c_{i\bar{\sigma}}c_{j\sigma}^\dagger - \langle c_{i\bar{\sigma}}c_{j\sigma} \rangle c_{i\sigma}c_{j\sigma}^\dagger \end{aligned} \quad (64)$$

Since we impose d-wave symmetry by mean of the d-wave γ_{ij} factor in Eq.(62), all the symmetry channels except the one associated to the d-wave symmetry $\langle c_{i\bar{\sigma}}c_{j\sigma} \rangle$ will be assumed to be negligible. θ_{ij} can therefore been seen as an anomalous d-wave superconductivity mean field parameter. Since we consider singlet pairing, we have

$$\langle c_{i\sigma}c_{i\bar{\sigma}}n_{j\sigma} \rangle = \langle c_{i\bar{\sigma}}^\dagger c_{i\sigma}^\dagger n_{j\sigma} \rangle \quad (65)$$

We can still apply translationnal invariance to treat p , n and e as a constant. We can do the same for θ , but because of d-wave symmetry θ is not the same along the x and y axis ($\theta_x = -\theta_y$). We will therefore only average on one axis in order to have a

non zero θ . The self-consistent equations remain the same for n and e since they are only one body correlations. However extending the basis changes the self-consistent equations of p_{ij} and θ_{ij} . We obtain (cf appendix F for details)

$$\begin{cases} p &= \frac{n^2}{4} - \frac{\rho_1 + \phi \rho_2}{1 - \phi^2} - \frac{\rho_1 - \rho_2}{1 - \phi} - \frac{\rho_3}{1 + \phi} \\ \theta &= \frac{\zeta}{1 + \phi} \end{cases} \quad (66)$$

With

$$\begin{cases} \phi &= \frac{2}{2-n}(C_0^{11} + C_0^{12}) + \frac{2}{n}(C_0^{12} + C_0^{22}) \\ \rho_1 &= \frac{2}{2-n}(C^{11} + C^{12})^2 + \frac{2}{n}(C^{22} + C^{12})^2 \\ \rho_2 &= \frac{2}{2-n}(C^{13} + C^{14})^2 + \frac{2}{n}(C^{23} + C^{24})^2 \\ \rho_3 &= \frac{4}{n(2-n)}(C^{11} + C^{12})(C^{22} + C^{12}) \\ \zeta &= \frac{2}{2-n}(C^{11} + C^{12})(C^{13} + C^{14}) \\ &+ \frac{2}{n}(C^{12} + C^{22})(C^{23} + C^{24}) \end{cases} \quad (67)$$

Let us note that this decoupling is not unique. Several choices can be made. These choices give similar results but tend to overestimate or underestimate some quantities, depending on which regime we consider [4]. Except for the larger \mathbf{M} and \mathbf{I} matrices and these changes in the self-consistent equation, everything else remains the same. The expression of κ from Eq. (28) remains unchanged, but will involve 4×4 matrices.

2. Results

On Fig. 8 we plot the bands for the Roth and COM2 solutions. There is a doubling of the bands due to the particle-hole symmetry of the basis: we have four distinct eigenvalues ϵ^l of the \mathbf{E} matrix verifying the property $\epsilon^1 = -\epsilon^3$ and $\epsilon^2 = -\epsilon^4$. Beside this doubling, the bands are almost unmodified compared to what we have without superconductivity. Only one difference can be seen: a gap opening at $(\pi, 0)$. We performed a zoom around zero energy in order to see the gap better on the insets. The presence of the gap also appears on the Fermi surface: there is less weight near the $(\pi, 0)$ compared to what we had in Fig. 2 without superconductivity.

On Fig. 9a, we plot the parameter θ as a function of the electron density n for the COM2 and the Roth solutions (COM1 solution has a vanishing θ for every electron density n). The dashed-line corresponds to the usual d-wave superconducting order parameter $\Delta_{ij}^d = \langle c_{i\sigma} c_{j\bar{\sigma}} \rangle$. We can recover it directly from

the correlation functions involving nearest-neighbors $C_{ij}^{nm} = \langle \psi_i^n (\psi_j^m)^\dagger \rangle$ using the following equation

$$\Delta_{ij}^d = C_{ij}^{13} + C_{ij}^{14} + C_{ij}^{23} + C_{ij}^{24} \quad (68)$$

The maximum of θ and Δ^d are at the same electron density. For the Roth solution this corresponds to $n=0.8$, while for the COM2 solution it is around $n=0.9$. We already showed that $n=0.8$ corresponds to the Van Hove singularity for the Roth solution in the discussion of Fig. 4 and 5. This is in agreement with other studies [15] [10]. We claim the same phenomenon occurs for the COM2 solution. In Fig. 8 we plotted the bands and Fermi surfaces for the COM2 solution at $n=0.9$ where superconductivity is maximum. Beside the gap opening, the band for COM2 exhibits some flatness at $(\pi, 0)$ (it is at least flatter than the Roth solution) and its Fermi Surface is almost diamond-like. We justified this claim by plotting the density of state at the Fermi energy as a function of electron density on Fig. 9b. Let us note we did not considered superconductivity to compute this density of state (in order to see the Van Hove singularity): this is why we do not have any superconducting gap. The density of states was computed using Eq. (51) at $\omega = 0$. The maximum of the density of states can be seen at $n=0.9$ for the COM2 solution. For the Roth solution a maximum can be found near half-filling but this maximum is associated with the extremum of the band and does not improve superconductivity because it is too close to half-filling. Another maximum is found at $n=0.8$ and corresponds to the flatness at $(\pi, 0)$ we already associated this with the Van Hove singularity. This is in agreement with our physical intuition: a high density of states means there are a lot of available electrons available to form Cooper pairs.

We checked that the θ parameter also verifies the following particle-hole symmetry

$$\theta \rightarrow \theta^* \quad (69)$$

In order to satisfy particle-hole symmetry, there must be another maximum of θ , therefore another Van Hove singularity in the electron doped regime. On Fig. 9b, we indeed see another peak both for superconductivity and the density of states in the $n > 1$ area. They correspond to the particle-hole symmetric of the peaks in the hole doped region.

In this method, the gap opening observed on the bands in Fig. 8 is of the order of Δ^d , as it is expected. The value of θ affects both superconductivity and the density n , since θ involves both quantities.

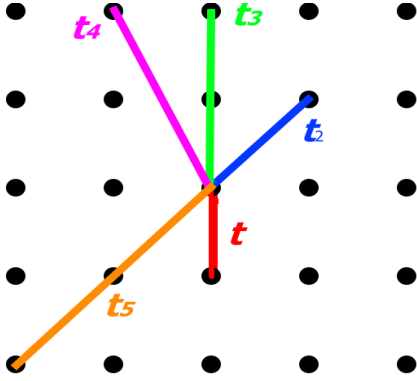


Figure 10: Square lattice with the considered hopping. We will consider long ranged hoppings up to t_5 . The associated values of these hoppings can be found in Table. I

IV. FURTHER HOPPINGS STUDY

We now want to consider the effect of higher hopping terms in order to get closer to more realistic materials. We want to see if the results we had with nearest-neighbours hoppings on the bands, the validity of the Luttinger theorem and superconductivity are modified by further hoppings. Including at least next nearest neighbors in the model is enough to break the particle-hole symmetry. We will only consider the Roth solution in this section, since COM2 and COM1 solutions have been studied with next-nearest neighbors in Ref. [13], and Roth presents Fermi surface closer to what is observed by ARPES for cuprates.

A. Effect of further nearest neighbours and bands analysis

From now on we will consider four different sets of tight-binding parameters all corresponding to a square lattice as in Fig. 10.

These tight-binding parameters correspond to cuprates Bi2212 and LSCO, which are strongly correlated. Their values, taken from Ref. [20], are given in Table I. They are such that the energy for a tight

binding model of a square lattice is given by

$$\begin{aligned} \epsilon_{tb}(k) = & 2t(\cos(k_x) + \cos(k_y)) \\ & + 4t_2\cos(k_x)\cos(k_y) \\ & + 2t_3(\cos(2k_x) + \cos(2k_y)) \\ & + 4t_4(\cos(k_x)\cos(2k_x) + \cos(2k_x)\cos(k_y)) \\ & + 4t_5\cos(2k_x)\cos(2k_y) \end{aligned} \quad (70)$$

In the following we will normalize every plots so we have $t=1$ (we will divide every tight binding parameter by t in absolute value).

	t	t_2	t_3	t_4	t_5
tb1	-0.2956	0.0818	-0.0260	-0.0280	0.0255
tb2	-0.3399	0.1184	-0.0397	0.0086	0.0006
tb3	-0.2941	0.0731	0.0048	-0.0325	0.0035
tb4	-0.3912	0.0370	-0.0294	-0.0350	-0.0087

Table I: Values of the 4 tight bindings we are going to consider. tb1 is based on an ARPES fit of Bi2212. tb2 corresponds to the bonding surface of Bi2212, tb3 is a modified version of tb2 to get a flatter band and tb4 corresponds to underdoped LSCO.

In this section we include hoppings up to t_5 and study the bands and Fermi surface behavior. With additional hopping terms, only the expression of the matrix \mathbf{M} changes. In addition to the α_{il}^1 parameter appearing in Eq. (32) higher hopping terms will appear in the \mathbf{M} matrix. It becomes

$$\begin{aligned} m_{ij}^{11} = & -\mu(1 - \frac{n_i}{2})\delta_{ij} - \sum_{k=1}^N t \left[\alpha_{ij}^k(1 - n_i + p_{ij}) + \delta_{ij} \sum_l \alpha_{il}^k e_{il} \right] \\ m_{ij}^{12} = & \sum_{k=1}^N t \left[\alpha_{ij}^k(\frac{n_i}{2} - p_{ij}) - \delta_{ij} \sum_l \alpha_{il}^k e_{il} \right] \\ m_{ij}^{22} = & -(\mu - U)\frac{n_i}{2}\delta_{ij} + \sum_{k=1}^N t \left[\alpha_{ij}^k p_{ij} - \delta_{ij} \sum_l \alpha_{il}^k e_{il} \right] \end{aligned} \quad (71)$$

where

$$\begin{cases} \alpha_{il}^N = 1 & \text{if } i \text{ and } l \text{ are } \overbrace{\text{next} \dots}^{N-1 \text{ times}} \text{-nearest neighbour} \\ \alpha_{il}^N = 0 & \text{Otherwise} \end{cases} \quad (72)$$

Each new hopping considered adds a term in the tight-binding Hamiltonian which is then added in the \mathbf{M} matrix. The parameters p and e depend on

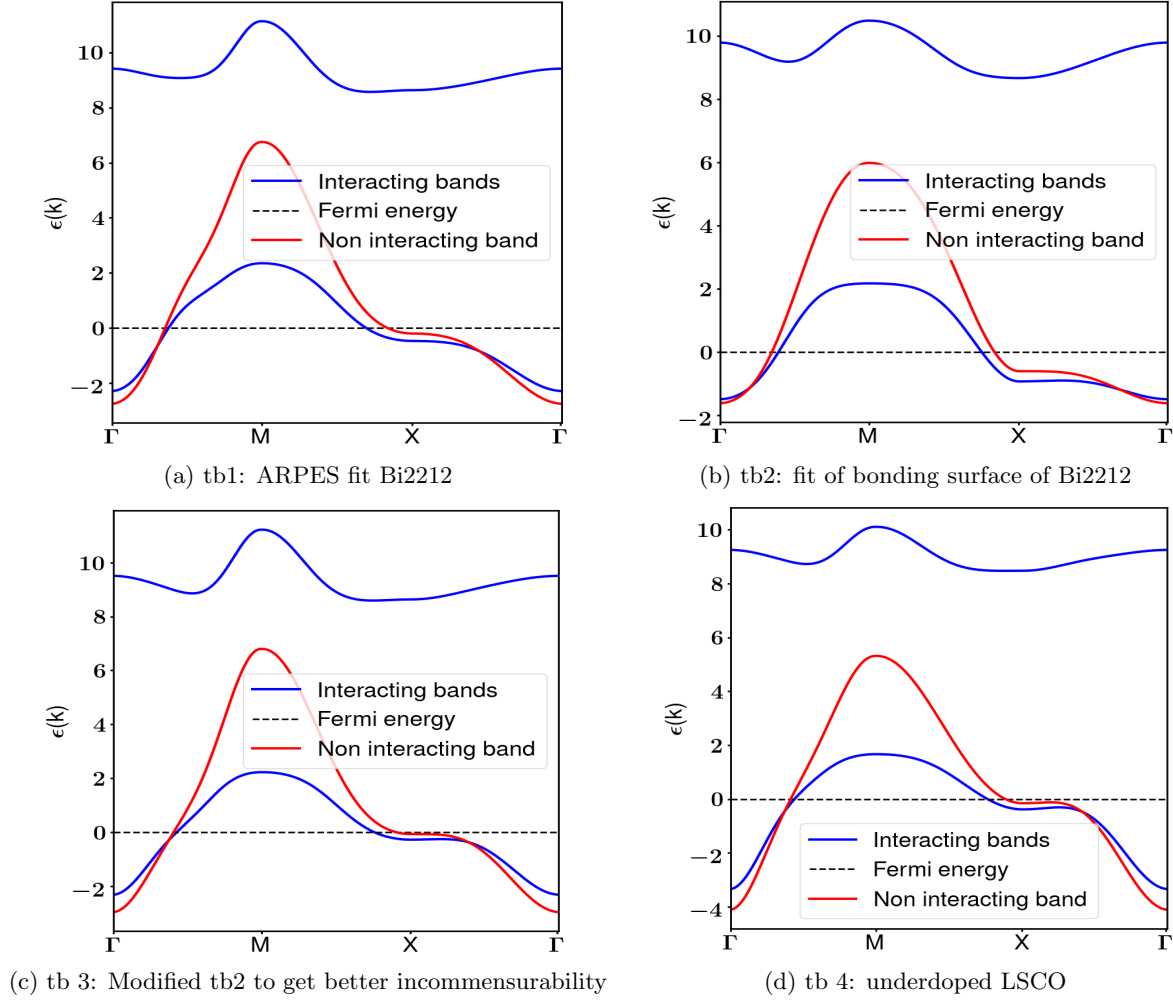


Figure 11: Bands renormalization using Roth minimization with hoppings up to order 5. The tight binding parameters are taken from Ref [20] and are given in table I. The red line is the non-interactive, tight binding dispersion. We are at 20% hole doping.

i - j , so we should make a distinction between e_{ij}^1 with i and j nearest neighbors (NN), e_{ij}^2 with i and j next nearest neighbors (NNN)... e_{ij}^n and p_{ij}^n will be associated with their corresponding hopping as in Fig. 10. Translational invariance (cf Eq. (34)) still allows us to treat $e^1, e^2, \dots, e^5, p^1, p^2, \dots, p^5$ as constants. Correlation functions $\mathbf{C}_{ij} = \langle \psi_i; \psi_j^\dagger \rangle$ are at different sites too, so we will also have to make a distinction in the self-consistent equations between \mathbf{C}^1 for NN, \mathbf{C}^2 for NNN and so on.

Fig. 11 presents the bands we obtain for Roth solutions for the four sets of tight-binding parameters

in Table. (I). In Fig. 12 and 13 we plotted respectively the Fermi surfaces obtained with the method and the Fermi surfaces of the non interactive tight-binding dispersions (corresponding to Eq. (70)).

In the hole doped regime, the Fermi surface we obtained from the Roth solution has the same general shape as the non interacting Fermi Surface. The composite operators method produces Fermi surfaces that appear to be smaller/larger than the tight-binding ones. This is in agreement with the violation of the Luttinger theorem observed with nearest-neighbour hopping, and indicates that it is still vi-

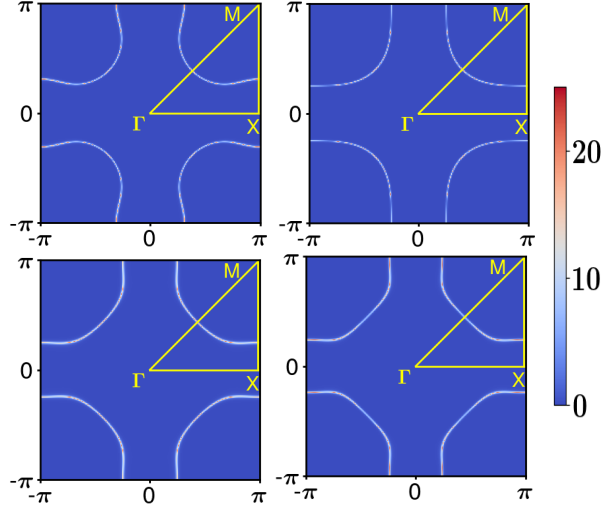


Figure 12: Fermi Surfaces renormalized by the composite operator methods using Roth minimization with the parameters of Ref [20]. We are at 20% hole doping. Top left: tb1, top right: tb2, bottom left: tb3, bottom right: tb4.

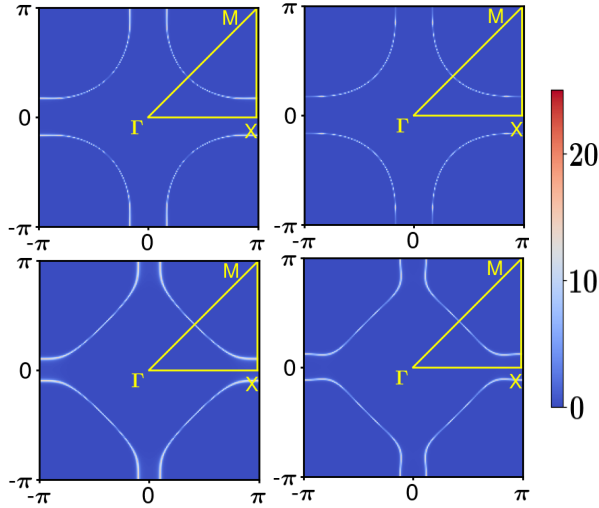


Figure 13: Non interacting (NI) Fermi Surfaces for the parameters of Ref [20] at 20% hole doping. Top left: tb1, top right: tb2, bottom left: tb3, bottom right: tb4.

olated with further hoppings. We checked the opposite situation is accordingly observed in electron doped area: the Fermi Surface obtained with the method is at a lower doping than the non interacting one. In the following we study the particle-hole

symmetry and the Luttinger theorem violation with next-nearest neighbours.

B. Particle-hole symmetry and Luttinger theorem with further neighbours

For the sake of simplicity we restrict ourselves to next-nearest neighbors in this part. In order to keep the full Hamiltonian invariant under particle-hole symmetry the following relation is needed

$$t_2 \rightarrow -t_2 \quad (73)$$

This is because the hopping term of the Hamiltonian $\sum_{ij} t_{ij} c_{i\sigma}^\dagger c_{j\sigma}$ transforms into $\sum_{ij} t_{ij} (-1)^{i+j} c_{i\sigma} c_{j\sigma}^\dagger$. For i and j next-nearest neighbour we have $(-1)^{i+j} = 1$. We obtain $-\sum_{\langle\langle i,j \rangle\rangle} t_2 c_{j\sigma}^\dagger c_{i\sigma}$, which has an additional minus sign, breaking the symmetry unless t_2 changes its sign with the transformation.

Hence, we know that at least next-nearest neighbors will break particle-hole symmetry (because t_2 is an external parameter that will always keep the same sign, therefore we do not verify Eq. (73)). The particle-hole transformation works the same for n and μ

$$\begin{aligned} n &\rightarrow 2 - n \\ \mu &\rightarrow U - \mu \end{aligned} \quad (74)$$

The main difference with the nearest-neighbors case comes from the necessity to differentiate the e and p parameters depending on the considered hopping. We already know the transformation for p^1 and e^1 . The only difference for p^2 and e^2 is $(-1)^{i+j} = 1$. p^2 will not be affected by the $(-1)^{i+j}$ coming from the transformation because it involves only two bodies operators. Thus only e^2 has an additional minus sign under the transformation, and we obtain the following relations

$$\begin{aligned} p^1 &\rightarrow 1 - n + p^1 \\ p^2 &\rightarrow 1 - n + p^2 \\ e^1 &\rightarrow -e^1 \\ e^2 &\rightarrow e^2 \end{aligned} \quad (75)$$

In Figs. 14a, 14b and 14c we plot the parameters μ , e and p as a function of doping for the four considered tight-binding parameters of Table. (I), only considering t and t_2 . Parameters e^2 and p^2

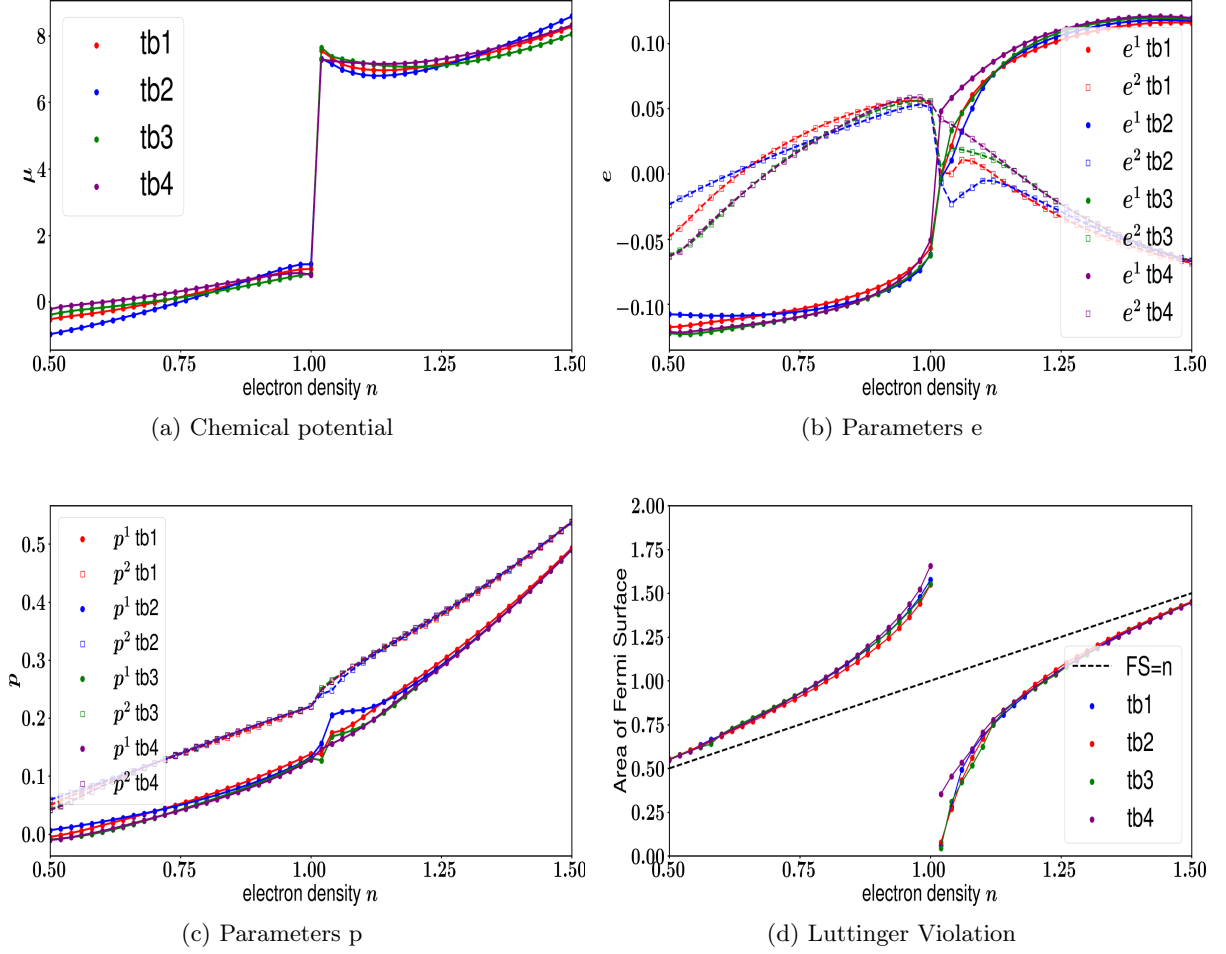


Figure 14: (a), (b) and (c) :Parameters as a function of doping for each tight binding with next nearest neighbors. The circles corresponds to p^1 and e^1 (NN) while the squares corresponds to p^2 and e^2 (NNN). (d) : Luttinger violation for each tight binding.

indeed break the particle-hole symmetry from Eq. (75). The chemical potential, as well as e^1 and p^1 behave as in the nearest neighbor case. We also checked that Eq. (75) is respected if we impose $t_2 \rightarrow -t_2$ when $n \rightarrow 2 - n$.

Finally we can again study the Luttinger theorem. In Fig. 14d, the area of the Fermi surface is plotted as a function of electron density. Interestingly we observe an analogous behavior as in the nearest-neighbor case. The Luttinger violation does not seem to be modified by next-nearest neighbors hoppings and is barely affected when we modify

tight-binding parameters. As already mentioned before, the Luttinger theorem is strongly violated around half filling and is recovered further away. This confirms why in the previous section the Fermi surfaces seemed to be at a higher doping than the electron density we considered when we are in the hole doped regime (and conversely, at a lower doping in the electron doped regime).

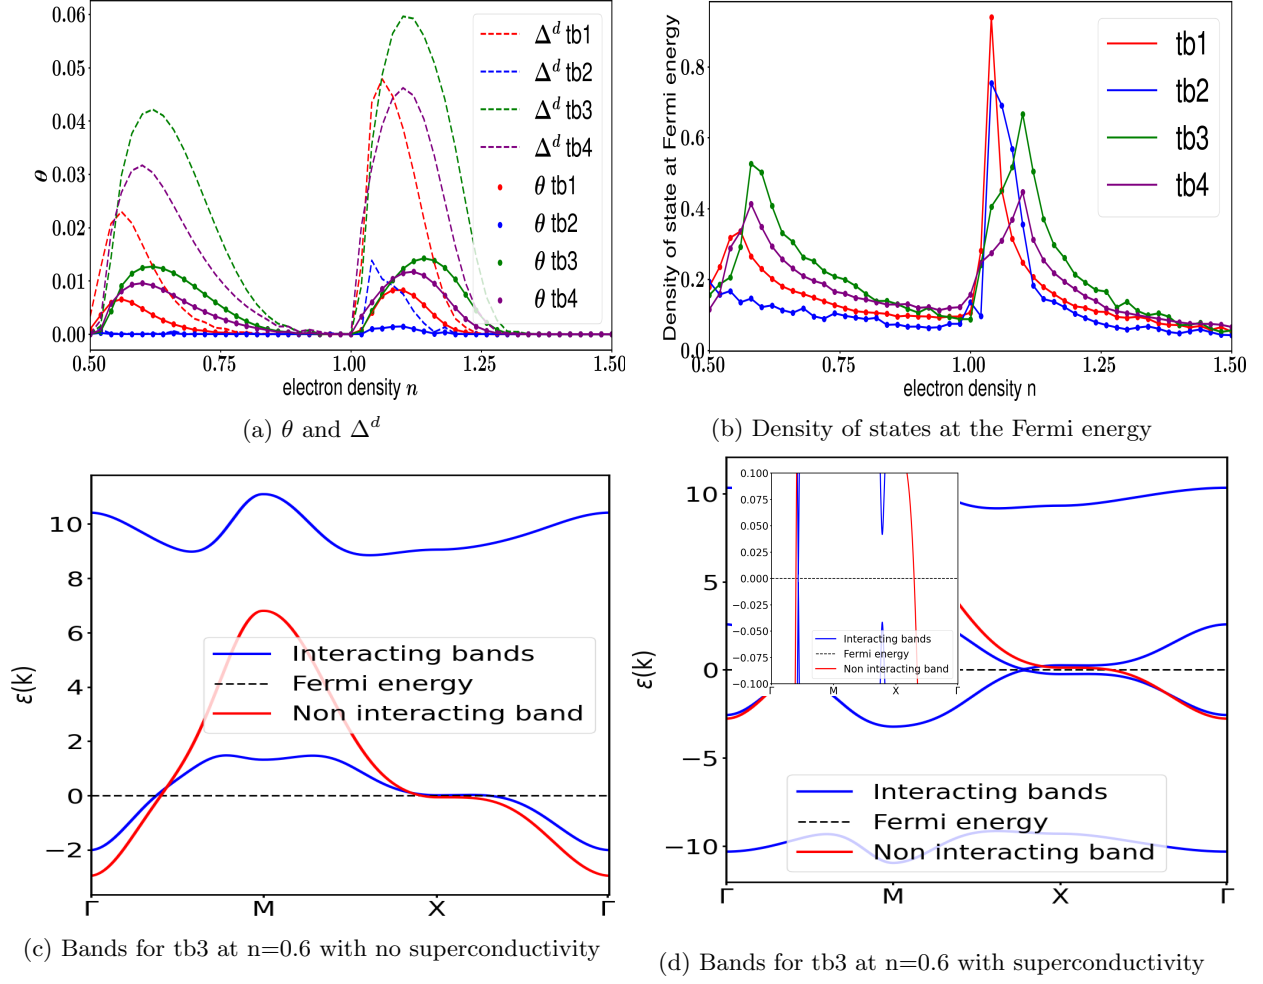


Figure 15: (a): Anomalous superconducting order parameter θ as a function of doping for the four sets of tight bindings parameters with Roth minimization. The dashed line corresponds to the usual d-wave superconducting order parameter we rebuilt from the correlation function. We are at $U=8t$. (b): Density of state (with no superconductivity in order to see the peaks) at the Fermi energy. The 2 peaks corresponds to the 2 Van Hove singularity in hole and electron doping respectively. To illustrate this the bottom plots (c) and (d) are the bands at the Van Hove singularity with tight binding parameters tb3 at $n=0.6$ respectively with: (c) no superconductivity, where we clearly see the flat band associated to Van Hove singularity (d) with superconductivity, where we see on the zoom in the inset the gap of the order of Δ^d .

C. Superconductivity, Van Hove singularity and density of state

Superconductivity can also be included in the model with more hoppings. In this section we include hoppings up until t_5 . We assume again a d-

wave symmetry and only consider nearest-neighbor pairing. As before, the \mathbf{M} and \mathbf{I} matrices become 4×4 and have the same symmetries as the nearest neighbours case. The \mathbf{I} matrix is independent of t and t' and is thus the same as before. The main difference is that the coefficients m_{ij}^{11} , m_{ij}^{12} and

m_{ij}^{22} are now given by Eq. (71). m_{ij}^{13} stays identical to its expression in the nearest neighbor case since we only consider superconductivity for nearest neighbors. Therefore m_{ij}^{13} is proportional to the θ parameter, defined the same way as before ($\theta_{ij} = \langle c_{i\uparrow} c_{i\downarrow} n_{j\sigma} \rangle$).

In Fig. 15a, the θ and Δ^d parameters are plotted as a function of electron density for the four tight-binding parameters with the Roth solution. Since we have included further neighbors, θ is not particle-hole symmetric anymore. In Fig. 15b, we plotted the density of states at the Fermi energy without superconductivity using Eq. (51) at $\omega = 0$ (in order to see the peaks with no superconducting gap). In Fig. 15c and 15d, we plotted without and with superconductivity the bands at electron densities corresponding to the maximum of the density of states for tb3 when the system is hole doped ($n \approx 0.6$). The bands with no superconductivity on 15c are flats at the Fermi energy. This proves that the maximum of Fig. 15b correspond to the Van Hove singularity. On 15d we see in the inset the gap at $(\pi, 0)$ is again of the order of $2\Delta^d$. The maximum of the θ and Δ^d parameters are thus at the same electron density as the Van Hove singularity. Hence, the situation is the same as in the nearest-neighbor case. In Table II we give the electron densities associated to the Van Hove singularities for the four sets of tight-binding parameters. Let us note there is no proportionality between the peak in the density of state and Δ^d : it is different for every set of tight-binding parameters. This is seemingly a consequence of the electronic correlations which are treated differently for each tight-binding parameters as a consequence of the main approximation of the method Eq. (24b).

	tb1	tb2	tb3	tb4
Van Hove (electron)	1.04	1.05	1.10	1.11
Van Hove (hole)	0.57	0.45	0.6	0.58

Table II: Electron density at which there is a Van Hove singularity at the chemical potential. At this values a flat band lies at the Fermi energy and the associated Fermi surface is diamond like. These singularities occur both in electron and in hole.

The most striking feature is that superconductivity in the method seems to be induced by the proximity of the Van Hove singularity. This was already the case with nearest neighbors but this property seems unaffected by further hopping terms. For cuprates there exist a consensus that antiferromag-

netism is the interaction necessary to explain the pairing mechanism [21]. This has also the advantage to explain why experimentally superconductivity is observed around 15% hole doping. Since this method predicts superconductivity only close to the Van Hove singularity, it is non zero at some doping values which does not correspond to what is expected. This flaw is maybe a consequence of the main hypothesis of the method (detailed in Appendix A): it is maybe necessary to consider dynamical corrections to the self-energy in order to observe a different behavior for superconductivity.

V. CONCLUSION

Considering only nearest neighbors first, three solutions have been isolated and studied: COM1, COM2 and Roth solutions. The Roth solution is the unique solution obtained if the self-consistency is performed on a parameter we called p and which enforced charge-charge, spin-spin and pair-pair correlations. This solution violates the Pauli principle because the correlation function $C_0^{12} = \langle \xi_{i\uparrow} \eta_{i\uparrow}^\dagger \rangle$ obtained after convergence is numerically non zero, even though it should be analytically because of the Pauli principle. COM1 and COM2 are two independent solutions obtained by performing a self-consistency imposing the correlation function C_0^{12} instead of the parameter p to enforce the Pauli principle.

We have performed a systematic comparison of the bands and Fermi surfaces for these three solutions. The three solutions present two Hubbard bands associated to the two eigenvalues of the method. COM1 is not renormalized by the interactions. COM2 has two hole pockets whatever the doping. Roth only has one hole pocket but a second small one appears close to half filling at (π, π) , possibly because antiferromagnetism has been neglected. Both Roth and COM2 solutions are insulators at half filling because the chemical potential lies in between the two Hubbard bands. The density of states for the Roth solution does not present the usual quasiparticle peak at $\omega = 0$ at half-filling and is in agreement with Determinantal quantum Monte-Carlo simulations.

The particle-hole symmetry is respected with nearest-neighbour hoppings: we checked that all solutions verify particle-hole relations, including the Roth solution. This result is different from what was predicted by ref. [9]: a solution of this method

can violate the Pauli principle and still be particle-hole symmetric. All solutions break the Luttinger close to half filling. This results is also in agreement with the determinantal quantum Monte-Carlo simulation [18]. The Luttinger theorem is only proven for weakly interacting systems. We think the Roth solution is the most physical. Although there is a violation of the Pauli principle, this solution exhibits Fermi surfaces typical of strongly correlated materials such as cuprates, contrary to COM1 and COM2. The COM1 solution consists of two tight-binding dispersions splitted by U and is not renormalized by interactions, whereas COM2 presents a second hole pocket which is not observed in ARPES experiments for Bi2212 and LSCO.

We extended the method to study d-wave superconductivity. Four composite operators are necessary to perform this study. The doubling of the basis leads to four eigenvalues, which are particle-hole symmetric because of the symmetry of the basis. We observed a gap opening at $(\pi, 0)$ for the COM2 and Roth solutions, of the order of the usual d-wave superconducting order parameter $\Delta_{ij}^d = \langle c_{i\uparrow}c_{j\downarrow} \rangle$. We only observe non zero superconductivity close to the Van Hove singularity. While this has already been predicted for the Roth solution [15], we showed that the COM2 solution behaves the same. We observed two Van Hove singularities for the COM2 and Roth solutions: one in the hole-doped and one in the electron-doped regime. Both singularities are a consequence of a flat band at $(\pi, 0)$. Lastly we noticed

$\Delta^d = \langle c_{i\uparrow}c_{j\downarrow} \rangle$ is three or four times bigger than θ . θ has no proportionality to Δ^d because it includes both a superconducting and a charge channel when we try to decouple it.

We studied the effect of longer ranged tight-binding parameters fitted from ARPES experiments on cuprates Bi2212 and LSCO from ref.[20], with the Roth minimization. If hole doped, the Fermi surfaces obtained with the method are similar to the non interacting Fermi surface, but at a higher doping. The opposite situation happens if the system is doped in electron: the Fermi surfaces appear similar but at a lower doping than the non interacting one. This is in agreement with the violation of the Luttinger theorem we still observe around the Mott transition. Adding further hoppings does not seem to modify this property. We checked that adding further hoppings breaks particle-hole symmetry. Finally, superconductivity also behaves mostly the same with further neighbors compared to the nearest neighbor case. The main difference is that Van Hove singularities as well as superconductivity peaks are moved at different electron density compared to the nearest-neighbors case. While this result is not at all in agreement with what was observed experimentally [5], it may be an indication that the main approximation done in this scheme needs to be refined. The dynamical corrections to the self-energy need to be considered in order to maybe have a behavior for superconductivity which is more in agreement with experimental observations.

-
- [1] E. Morosan, D. Natelson, A. H. Nevidomskyy, and Q. Si, “Strongly Correlated Materials,” *Advanced Materials*, vol. 24, pp. 4896–4923, Sept. 2012. arXiv:1309.4473 [cond-mat].
- [2] S. Sachdev, “Order and quantum phase transitions in the cuprate superconductors,” *Reviews of Modern Physics*, vol. 75, pp. 913–932, July 2003. arXiv:cond-mat/0211005.
- [3] J. Bardeen, L. N. Cooper, and J. R. Schrieffer, “Theory of Superconductivity,” *Physical Review*, vol. 108, pp. 1175–1204, Dec. 1957.
- [4] J. G. Bednorz and K. A. Müller, “Perovskite-type oxides—the new approach to high- T_c superconductivity,” *Rev. Mod. Phys.*, vol. 60, pp. 585–600, Jul 1988.
- [5] M. R. Norman and C. Pepin, “The Electronic Nature of High Temperature Cuprate Superconductors,” *Reports on Progress in Physics*, vol. 66, pp. 1547–1610, Oct. 2003. arXiv:cond-mat/0302347.
- [6] A. Georges, G. Kotliar, W. Krauth, and M. J. Rozenberg, “Dynamical mean-field theory of strongly correlated fermion systems and the limit of infinite dimensions,” *Reviews of Modern Physics*, vol. 68, pp. 13–125, Jan. 1996.
- [7] E. H. Lieb and F. Y. Wu, “The one-dimensional Hubbard model: A reminiscence,” *Physica A: Statistical Mechanics and its Applications*, vol. 321, pp. 1–27, Apr. 2003. arXiv:cond-mat/0207529.
- [8] J. Hubbard, “Electron correlations in narrow energy bands,” *Proceedings of the Royal Society of London. Series A. Mathematical and Physical Sciences*, vol. 276, pp. 238–257, Nov. 1963.
- [9] A. Avella, F. Mancini, D. Villani, L. Siurakshina, and V. Y. Yushankhai, “The Hubbard Model in the Two-Pole Approximation,” *International Journal of Modern Physics B*, vol. 12, pp. 81–97, Jan. 1998.

- [10] J. Beenen and D. M. Edwards, “Superconductivity in the two-dimensional Hubbard model,” *Physical Review B*, vol. 52, pp. 13636–13651, Nov. 1995.
- [11] L. M. Roth, “Electron Correlation in Narrow Energy Bands. I. The Two-Pole Approximation in a Narrow S Band,” *Physical Review*, vol. 184, pp. 451–459, Aug. 1969.
- [12] A. Avella and F. Mancini, “Anomalous Self-Energy Features in the 2D Hubbard Model,” *Acta Physica Polonica A*, vol. 113, pp. 395–398, Jan. 2008.
- [13] A. Avella, F. Mancini, D. Villani, and H. Matsumoto, “The two-dimensional t-t'-U model as a minimal model for cuprate materials,” *The European Physical Journal B*, vol. 20, pp. 303–311, Apr. 2001.
- [14] E. J. Calegari, A. C. Lausmann, S. G. Magalhaes, C. M. Chaves, and A. Troper, “Pseudogap and the specific heat of high T_c superconductors: a Hubbard model in a n-pole approximation,” *Journal of Physics: Conference Series*, vol. 592, p. 012075, Mar. 2015. arXiv:1412.4692 [cond-mat].
- [15] E. J. Calegari, S. G. Magalhaes, and A. A. Gomes, “Superconductivity in a two dimensional extended Hubbard model,” *The European Physical Journal B*, vol. 45, pp. 485–496, June 2005. arXiv:cond-mat/0505427.
- [16] A. Avella and F. Mancini, “The Composite Operator Method (COM),” vol. 171, pp. 103–141, 2012. arXiv:1112.1103 [cond-mat].
- [17] D. Bergeron, D. Chowdhury, M. Punk, S. Sachdev, and A.-M. S. Tremblay, “Breakdown of Fermi liquid behavior at the $(\pi, \pi) = 2k_F$ spin-density wave quantum-critical point: the case of electron-doped cuprates,” *Physical Review B*, vol. 86, p. 155123, Oct. 2012. arXiv:1207.1106 [cond-mat].
- [18] I. Osborne, T. Paiva, and N. Trivedi, “Fermi-surface Reconstruction in the Repulsive Fermi-Hubbard Model,” June 2020. arXiv:2001.07197 [cond-mat].
- [19] J. M. Luttinger, “Fermi Surface and Some Simple Equilibrium Properties of a System of Interacting Fermions,” *Physical Review*, vol. 119, pp. 1153–1163, Aug. 1960.
- [20] M. R. Norman, “Linear response theory and the universal nature of the magnetic excitation spectrum of the cuprates,” *Physical Review B*, vol. 75, p. 184514, May 2007.
- [21] L. Taillefer, “Scattering and Pairing in Cuprate Superconductors,” *Annual Review of Condensed Matter Physics*, vol. 1, pp. 51–70, Aug. 2010.
- [22] T. D. Stanescu, I. Martin, and P. Phillips, “d x 2 - y 2 pairing of composite excitations in the two-dimensional Hubbard model,” *Physical Review B*, vol. 62, pp. 4300–4308, Aug. 2000.

APPENDIX A : PHYSICAL MEANING OF THE APPROXIMATION ON THE CURRENT

In order to be able to compute the \mathbf{M} matrix with the full Hubbard Hamiltonian in the strongly coupled regime, we neglected all terms in the current (Eq. (8)) that are not along ψ . Though afterwards we computed explicitly the currents, the terms orthogonal to ψ are neglected through the self consistency because we use the relation $\mathbf{M} = \mathbf{E}\mathbf{I}$, which is a consequence of our hypothesis.

To better understand the consequences of such approximation we need to consider the self energy. To do so, we follow the step of Ref. [12]. Let's therefore consider the full expression of the current

$$J_i = \sum_l \mathbf{E}_{il} \psi_l + \delta\phi_i \quad (76)$$

Our approximation, $\langle \{\delta\phi_i, \psi_j^\dagger\} \rangle = 0$ allows us to write $\mathbf{E}_{ij} = \sum_l \mathbf{M}_{il} \cdot \mathbf{I}_{lj}^{-1}$. From this, we know the 0-th order Green's function is defined for $\delta\phi = 0$ by $\mathbf{S}^0 = \frac{\mathbf{I}}{\omega - \mathbf{E}}$.

Without this approximation, the full equations of motion for the composite Green's function is

$$\frac{d}{d\tau} \mathbf{S}_{ij}(\tau) = \delta(\tau) \langle \{\psi_i(\tau); \psi_j^\dagger\} \rangle + \theta_H(\tau) \langle \{J_i(\tau); \psi_j^\dagger\} \rangle \quad (77)$$

In Fourier space, and with Eq. (76), this becomes

$$\mathbf{S}_{ij}(\omega) = \mathbf{S}_{ij}^0(\omega) + \mathbf{I}_{ij}^{-1} \mathbf{S}_{ij}^0(\omega) \langle \{\delta\phi_i(\omega); \psi_j^\dagger(\omega)\} \rangle \quad (78)$$

Now we know that

$$\frac{d}{d\tau} \psi_i^\dagger = \sum_l \mathbf{E}_{il} \psi_l^\dagger + \delta\phi_i \quad (79)$$

Therefore in Fourier space

$$\psi_i^\dagger(\omega) = (\omega - \mathbf{E}_{ij} + i0^+)^{-1} \delta\phi_i = \mathbf{S}_{ij}^0(\omega) \mathbf{I}_{ij}^{-1} \delta\phi_i \quad (80)$$

Hence we can inject this in the equations of motion on \mathbf{S}_{ij} to get

$$\mathbf{S}_{ij}(\omega) = \mathbf{S}_{ij}^0(\omega) + \mathbf{S}_{ij}^0(\omega) \mathbf{I}_{ij}^{-1} \langle \{\delta\phi_i; \delta\phi_j^\dagger\} \rangle \mathbf{I}_{ij}^{-1} \mathbf{S}_{ij}^0(\omega) \quad (81)$$

We can introduce the scattering matrix \mathbf{T}

$$\mathbf{T} = \mathbf{I}^{-1} \langle \{\delta\phi; \delta\phi^\dagger\} \rangle \mathbf{I}^{-1} \quad (82)$$

We therefore obtain the familiar form

$$\mathbf{S} = \mathbf{S}^0 + \mathbf{S}^0 \mathbf{T} \mathbf{S}^0 \quad (83)$$

We can introduce the self-energy through the relation $\mathbf{T} \mathbf{S}^0 = \mathbf{I}^{-1} \mathbf{\Sigma} \mathbf{S}$, and obtain in reciprocal space the Dyson equation

$$\mathbf{S}(k, \omega) = \frac{\mathbf{I}}{\omega - \mathbf{E}(k) - \mathbf{\Sigma}(k, \omega) + i0^+} \quad (84)$$

From this equation we clearly see the consequences of our approximation. Neglecting $\delta\phi$ in the current, which are all the contributions orthogonal to ψ , is equivalent to neglecting $\mathbf{\Sigma}(k, \omega)$, therefore working with a static self energy. This approximation neglects all dynamical dependencies of the self energy.

APPENDIX B : SPECTRAL REPRESENTATION AND RESIDUE THEOREM OF THE COMPOSITE GREEN'S FUNCTION

We start from the following expression for the composite Green's function

$$\mathbf{S}_{ij}(\omega) = \frac{\mathbf{I}_{ij}}{\omega - \mathbf{E}_{ij} + i0^+} \quad (85)$$

\mathbf{E} is diagonalizable, its eigenvalues are called ϵ^1 and ϵ^2 , and we can rewrite this as

$$\begin{aligned} \mathbf{S}_{ij}(\omega) &= \frac{\mathbf{I}_{ij} \text{Com}(\omega - \mathbf{E}_{ij} + i0^+)^T}{\det(\omega - \mathbf{E}_{ij} + i0^+)} \\ &= \frac{\mathbf{I}_{ij} \text{Com}(\omega - \mathbf{E}_{ij} + i0^+)^T}{(\omega - \epsilon_{ij}^1 + i0^+)(\omega - \epsilon_{ij}^2 + i0^+)} \end{aligned} \quad (86)$$

Where $\text{Com}(\mathbf{A})$ is the cofactors matrix of \mathbf{A} . We now want to apply residue theorem.

We consider the function $\frac{\mathbf{S}_{ij}(z)}{z - \omega + i\eta}$ with η small. Since we know any Green's functions, including \mathbf{S} , is analytical on the upper half-circle of the complex plane we integrate over this contour C_u . The poles of \mathbf{S} are real and we have another pole at $z = \omega - i\eta$, which is on the lower half-circle of the complex plane. Therefore no poles lies in C_u and we have

$$\oint_{C_u} \frac{\mathbf{S}_{ij}(z)}{z - \omega - i\eta} dz = 0 \quad (87)$$

We now use the previous expression of \mathbf{S} to get

$$\oint_{C_u} \frac{\mathbf{I}_{ij} \text{Com}(z - \mathbf{E}_{ij})^T}{\det(z - \mathbf{E})(z - \omega - i\eta)} dz = 0 \quad (88)$$

Replacing the integrals by the sum of all the residues, we obtain

$$\sum_{z_0 \in \mathcal{P}} \text{Res} \left(\frac{\mathbf{I}_{ij} \text{Com}(z - \mathbf{E}_{ij})^T}{(z - \epsilon_{ij}^1)(z - \epsilon_{ij}^2)(z - \omega - i\eta)}, z \rightarrow z_0 \right) = 0 \quad (89)$$

In this equation, \mathcal{P} denotes the poles of $\frac{\mathbf{S}_{ij}(z)}{z - \omega + i\eta}$. It has three poles

$$\begin{aligned} z_1 &= \omega + i\eta \\ z_2 &= \epsilon_{ij}^1 \\ z_3 &= \epsilon_{ij}^2 \end{aligned} \quad (90)$$

These poles are all non degerated, meaning the residue can easily be computed using

$$\text{Res}(f(z), z \rightarrow z_0) = \lim_{z \rightarrow z_0} (z - z_0) f(z) \quad (91)$$

Doing so leads to

$$\begin{aligned} 0 &= \frac{\mathbf{I} \text{Com}(\omega - \mathbf{E}_{ij} + i\eta)^T}{(\omega - \epsilon_{ij}^1 + i\eta)(\omega - \epsilon_{ij}^2 + i\eta)} \\ &+ \frac{\mathbf{I}_{ij} \text{Com}(\epsilon_{ij}^1 - \mathbf{E}_{ij})^T}{(\epsilon_{ij}^1 - \epsilon_{ij}^2)(\epsilon_{ij}^1 - \omega - i\eta)} \\ &+ \frac{\mathbf{I}_{ij} \text{Com}(\epsilon_{ij}^2 - \mathbf{E}_{ij})^T}{(\epsilon_{ij}^2 - \epsilon_{ij}^1)(\epsilon_{ij}^2 - \omega - i\eta)} \end{aligned} \quad (92)$$

We recognize the first term can be rewritten as

$$\frac{\mathbf{I}_{ij} \text{Com}(\omega - \mathbf{E}_{ij} + i\eta)^T}{\det(\omega - \mathbf{E}_{ij} + i\eta)} = \mathbf{I}_{ij}(\omega - \mathbf{E}_{ij} + i\eta)^{-1} = \mathbf{S}_{ij}(\omega + i\eta) \quad (93)$$

Finally we rearrange the equation (and evaluate \mathbf{S} in $\omega - i\eta$ to get retarded composite Green's func-

tions) to recover the desired decomposition (replacing η by 0^+)

$$\mathbf{S}_{ij}(\omega) = \frac{\mathbf{I}_{ij} \text{Com}(\epsilon_{ij}^2 - \mathbf{E}_{ij})^T}{(\epsilon_{ij}^1 - \epsilon_{ij}^2)(\omega - \epsilon_{ij}^2 + i0^+)} - \frac{\mathbf{I}_{ij} \text{Com}(\epsilon_{ij}^1 - \mathbf{E}_{ij})^T}{(\epsilon_{ij}^1 - \epsilon_{ij}^2)(\omega - \epsilon_{ij}^1 + i0^+)} \quad (94)$$

We pose

$$\kappa_{ij}^a = (-1)^{a+1} \frac{\mathbf{I}_{ij} \text{Com}(\epsilon_{ij}^a - \mathbf{E}_{ij})^T}{(\epsilon_{ij}^1 - \epsilon_{ij}^2)} \quad (95)$$

With $a \in \{1, 2\}$ to obtain the form given in Eq. (27).

APPENDIX C : COMPUTATIONS OF M AND I MATRICES

In this section we first derive from the composite operator algebra the currents, then we use them to obtain the \mathbf{M} and \mathbf{I} matrices. Let us start by writing few of the most useful commutation relation that we used for the computations

$$\begin{aligned} \{\eta_{i\sigma}; \eta_{j\sigma'}^\dagger\} &= \delta_{ij}(\delta_{\sigma\sigma'} n_{i\bar{\sigma}} - \delta_{\sigma\bar{\sigma}'} c_{i\sigma}^\dagger c_{i\bar{\sigma}}) \\ \{\xi_{i\sigma}; \xi_{j\sigma'}^\dagger\} &= \delta_{ij}(\delta_{\sigma\sigma'}(1 - n_{i\bar{\sigma}}) + \delta_{\sigma\bar{\sigma}'} c_{i\sigma}^\dagger c_{i\bar{\sigma}}) \\ \{\xi_{i\sigma}; \eta_{j\sigma'}^\dagger\} &= 0 \\ \{c_{i\sigma}; \xi_{j\sigma'}^\dagger\} &= \delta_{ij}(\delta_{\sigma\sigma'}(1 - n_{j\sigma}) + \delta_{\sigma\bar{\sigma}'} c_{i\sigma}^\dagger c_{i\bar{\sigma}'}) \\ \{c_{i\sigma}; \eta_{j\sigma'}^\dagger\} &= \delta_{ij}(\delta_{\sigma\sigma'} n_{i\bar{\sigma}} - \delta_{\sigma\bar{\sigma}'} c_{i\sigma}^\dagger c_{i\bar{\sigma}'}) \\ \{c_{i\sigma}; \xi_{j\sigma'}\} &= \delta_{ij} \delta_{\sigma\bar{\sigma}'} c_{i\sigma'} c_{i\bar{\sigma}'} \\ \{c_{i\sigma}; \eta_{j\sigma'}\} &= -\delta_{ij} \delta_{\sigma\bar{\sigma}'} c_{i\sigma'} c_{i\bar{\sigma}'} \end{aligned} \quad (96)$$

From this we can explicitly compute the commutators of the composite operators ψ with the hamiltonian to get the following currents

$$\begin{aligned} j_i^1 &= -\mu \xi_{i\sigma} - \sum_l t_{il} \left(c_{l\sigma} - n_{i\bar{\sigma}} c_{l\sigma} + S_i^- c_{l\bar{\sigma}} - \Delta_i c_{l\bar{\sigma}}^\dagger \right) \\ j_i^2 &= -(\mu - U) \eta_{i\sigma} + \sum_l t_{il} \left(-n_{i\bar{\sigma}} c_{l\sigma} + S_i^- c_{l\bar{\sigma}} - \Delta_i c_{l\bar{\sigma}}^\dagger \right) \end{aligned} \quad (97)$$

The $\mathbf{I} = \langle \{\psi; \psi^\dagger\} \rangle$ and $\mathbf{M} = \langle \{j; \psi^\dagger\} \rangle$ matrices can be explicitly computed from these expressions.

Note that

$$\begin{aligned} \mathbf{I}_{ij}^{12} &= \mathbf{I}_{ij}^{21} \\ \mathbf{M}_{ij}^{12} &= \mathbf{M}_{ij}^{12} \end{aligned} \quad (98)$$

APPENDIX D : ROTH DECOUPLING AND COMPUTATION OF P

In this appendix we derive the self-consistent equation of

$$p(i-j) = \langle n_{i\uparrow} n_{j\uparrow} \rangle + \langle S_i^+ S_j^- \rangle - \langle \Delta_i \Delta_j^* \rangle \quad (99)$$

We will not detail the main decoupling scheme as it is already done in the main text but rather focus on the algebraic computations and give the form of the equations for the charge-charge and spin-spin term.

A. Pair-pair term

Since the general method has already been detailed in the text for this term we start directly from eq. (44) and compute $f_{kjl}^n = \langle \{\psi_k^n; c_{j\downarrow} \Delta_l^*\} \rangle$. Computing the anticommutators using the algebraic relations given in appendix 4 leads to

$$\begin{aligned} f_{kjl}^1 &= \delta_{kj} \langle \Delta_k \Delta_l^* \rangle + \delta_{kl} (C_{kj}^{21} + C_{kj}^{22}) \\ f_{kjl}^2 &= -\delta_{kj} \langle \Delta_k \Delta_l^* \rangle + \delta_{kl} (C_{kj}^{11} + C_{kj}^{12}) \end{aligned} \quad (100)$$

Eq. (44) then becomes

$$\begin{aligned} \langle c_{i\uparrow} c_{j\downarrow} \Delta_l^* \rangle &= \frac{2}{2-n} \sum_k (C_{ik}^{11} + C_{ik}^{12}) \\ &[\delta_{kj} \langle \Delta_k \Delta_l^* \rangle + \delta_{kl} (C_{kj}^{21} + C_{kj}^{22})] \\ &+ \frac{2}{n} \sum_k (C_{ik}^{12} + C_{ik}^{22}) \\ &[\delta_{kj} \langle \Delta_k \Delta_l^* \rangle + \delta_{kl} (C_{kj}^{21} + C_{kj}^{22})] \end{aligned} \quad (101)$$

Simplifying this equation and setting $i=j$ leads to

$$\langle \Delta_i \Delta_l^* \rangle = \frac{4}{n(2-n)} \frac{(C_{il}^{11} + C_{il}^{12})(C_{il}^{22} + C_{il}^{21})}{1 - \frac{2}{2-n}(C_0^{11} + C_0^{12}) + \frac{2}{n}(C_0^{21} + C_0^{22})} \quad (102)$$

Which is the form in the main text. We pose

$$\phi = -\frac{2}{2-n} (C_0^{11} + C_0^{12}) + \frac{2}{n} (C_0^{21} + C_0^{22}) \quad (103)$$

Replacing C_0^{11} and C_0^{22} by their definitions allows us to express these correlations function explicitly as a function of n . We don't explicit C_0^{12} however, else it will be zero while it is not numerically: C_0^{12} should stay in the numerical minimization process to obtain our results. Doing so leads to the following expression for ϕ

$$\phi = \frac{n^2 - 4(\frac{n}{2} - \langle n_{i\uparrow} n_{i\downarrow} \rangle) - C_0^{12}}{n(2-n)} \quad (104)$$

With our notations the pair-pair term becomes

$$\langle \Delta_i \Delta_l^* \rangle = \frac{\rho_3}{1+\phi} \quad (105)$$

B. Spin-Spin term

The spin-spin term is defined as $\langle S_i^+ S_l^- \rangle = \langle c_{i\uparrow}^\dagger c_{i\downarrow} c_{l\downarrow}^\dagger c_{l\uparrow} \rangle$. In order to have our basis element as the first term, we rewrite it as

$$\langle S_i^+ S_l^- \rangle = -\langle c_{i\uparrow}^\dagger c_{i\downarrow} c_{l\uparrow} c_{l\downarrow}^\dagger \rangle = -\langle c_{l\uparrow} c_{l\downarrow}^\dagger c_{i\uparrow}^\dagger c_{i\downarrow} \rangle \quad (106)$$

We therefore introduce the following Green's functions (setting $\tau' = 0$)

$$\begin{cases} F_{ijl}(\tau) = \langle \langle \xi_{i\uparrow}(\tau); c_{j\downarrow}^\dagger S_l^+ \rangle \rangle \\ G_{ijl}(\tau) = \langle \langle \eta_{i\uparrow}(\tau); c_{j\downarrow}^\dagger S_l^+ \rangle \rangle \end{cases} \quad (107)$$

The next steps are the same as with the pair-pair term. The only difference lies in the definition of f^n in the resulting equations of motion. For the spin-spin term it is defined as $f_{kjl}^n = \langle \{ \psi_k^n; c_{j\downarrow}^\dagger S_l^+ \} \rangle$. Hence we arrive at the following equation

$$\begin{aligned} \langle c_{i\uparrow} c_{j\downarrow}^\dagger S_l^+ \rangle &= \frac{2}{2-n} \sum_k (C_{ik}^{11} + C_{ik}^{12}) f_{kjl}^1 \\ &+ \frac{2}{n} \sum_k (C_{ik}^{12} + C_{ik}^{22}) f_{kjl}^2 \end{aligned} \quad (108)$$

A computation of the f^n leads to

$$\begin{aligned} f_{kjl}^1 &= \delta_{kj} \langle S_k^- S_l^+ \rangle - \delta_{kl} (C_{kj}^{11} + C_{kj}^{12}) \\ f_{kjl}^2 &= -\delta_{kj} \langle S_k^- S_l^+ \rangle - \delta_{kl} (C_{kj}^{12} + C_{kj}^{22}) \end{aligned} \quad (109)$$

Therefore by replacing f by their explicit expression we obtain

$$\begin{aligned} \langle c_{i\uparrow} c_{j\downarrow}^\dagger S_l^+ \rangle &= \frac{2}{2-n} \sum_k (C_{ik}^{11} + C_{ik}^{12}) \\ &[\delta_{kj} \langle S_k^- S_l^+ \rangle - \delta_{kl} (C_{kj}^{11} + C_{kj}^{12})] \\ &+ \frac{2}{n} \sum_k (C_{ik}^{12} + C_{ik}^{22}) \\ &[-\delta_{kj} \langle S_k^- S_l^+ \rangle - \delta_{kl} (C_{kj}^{12} + C_{kj}^{22})] \end{aligned} \quad (110)$$

Which we can again simplify and set $i=j$ to obtain

$$\langle S_i^- S_l^+ \rangle = -\frac{\frac{2}{2-n} (C_{il}^{11} + C_{il}^{12})^2 + \frac{2}{n} (C_{il}^{12} + C_{22}^{il})^2}{1 - \frac{2}{2-n} (C_0^{11} + C_0^{12}) + \frac{2}{n} (C_0^{12} + C_0^{22})} \quad (111)$$

Which become with our notations

$$\langle S_i^- S_l^+ \rangle = \frac{\rho_1}{1-\phi} \quad (112)$$

C. Charge-Charge term

As we did for the $\langle S_i^- S_l^+ \rangle$ term we need to commute the charge charge term so the first element can be decomposed using our spinor. We then rewrite

$$\langle c_{i\uparrow}^\dagger c_{i\uparrow} n_{l\uparrow} \rangle = \frac{n}{2} - \langle c_{i\uparrow} c_{i\uparrow}^\dagger n_{l\uparrow} \rangle \quad (113)$$

We introduce the following Green's functions

$$\begin{cases} F_{ijl}(\tau) = \langle \langle \xi_{i\uparrow}(\tau); c_{j\uparrow}^\dagger n_{l\uparrow} \rangle \rangle \\ G_{ijl}(\tau) = \langle \langle \eta_{i\uparrow}(\tau); c_{j\uparrow}^\dagger n_{l\uparrow} \rangle \rangle \end{cases} \quad (114)$$

Once again the general form of the equation for $\langle c_{i\sigma} c_{i\sigma}^\dagger n_{l\sigma} \rangle$ will be the same as for the other 2 terms. However the definition of the involved f_{kjl}^n will not be the same. We compute $f_{kjl}^n = \langle \{ \psi_k^n; c_{j\uparrow}^\dagger n_{l\uparrow} \} \rangle$

$$f_{kjl}^1 = \delta_{kj} \left(\frac{n}{2} - \langle n_{k\downarrow} n_{l\uparrow} \rangle \right) + \delta_{kl} (C_{kj}^{11} + C_{kj}^{12}) \quad (115)$$

$$f_{kjl}^2 = \delta_{kj} \langle n_{k\downarrow} n_{l\uparrow} \rangle + \delta_{kl} (C_{kj}^{12} + C_{kj}^{22})$$

We hence obtain

$$\langle n_{i\uparrow} n_{l\uparrow} \rangle = \frac{n}{2} - \rho_1 - \phi \langle n_{i\uparrow} n_{l\downarrow} \rangle + \frac{n}{2-n} (C_0^{11} + C_0^{12}) \quad (116)$$

We don't know how to express $\langle n_{i\downarrow}n_{l\uparrow} \rangle$ as a function of the correlations functions. So we need to redo this decoupling on this term. This time we use

$$\langle n_{i\downarrow}n_{l\uparrow} \rangle = \frac{n}{2} - \langle c_{l\uparrow}c_{i\uparrow}^\dagger n_{i\downarrow} \rangle \quad (117)$$

We therefore introduce

$$\begin{cases} F_{ijl}(\tau) = \langle \langle \xi_{i\uparrow}(\tau); c_{j\uparrow}^\dagger n_{l\downarrow} \rangle \rangle \\ G_{ijl}(\tau) = \langle \langle \eta_{i\uparrow}(\tau); c_{j,\uparrow}^\dagger n_{l\downarrow} \rangle \rangle \end{cases} \quad (118)$$

The $f_{kjl}^n = \langle \psi_k^n, c_{j\uparrow}^\dagger n_{l\downarrow} \rangle$ are given by

$$\begin{aligned} f_{kjl}^1 &= \delta_{kj} \left(\frac{n}{2} - \langle n_{i\downarrow}n_{l\downarrow} \rangle \right) \\ f_{kjl}^2 &= \delta_{kj} \langle n_{i\downarrow}n_{l\downarrow} \rangle \end{aligned} \quad (119)$$

Using the paramagnetic assumption we have $\langle n_{i\uparrow}n_{l\uparrow} \rangle = \langle n_{i\downarrow}n_{l\downarrow} \rangle$, leading to

$$\langle n_{i\uparrow}n_{l\downarrow} \rangle = \frac{n}{2} - \phi \langle n_{i\uparrow}n_{l\uparrow} \rangle + \frac{n}{2-n} (C_0^{11} + C_0^{12}) \quad (120)$$

If we inject this in the equation of $\langle n_{i\uparrow}n_{l\uparrow} \rangle$, we obtain

$$\langle n_{i\uparrow}n_{l\uparrow} \rangle = -\rho_1 + \phi^2 \langle n_{i\uparrow}n_{l\uparrow} \rangle + \frac{n}{2-n} (C_0^{11} + C_0^{12})(1-\phi) \quad (121)$$

The last term can be simplified. An explicit computations of the C_0 leads to $C_0^{11} + C_0^{12} = 1 - n + \langle n_{i\uparrow}n_{i\downarrow} \rangle$, allowing us to show the last term is in fact just equal to $\frac{n^2}{4}$. We therefore obtain

$$\langle n_{i\uparrow}n_{l\downarrow} \rangle = \frac{n^2}{4} - \frac{\rho_1}{1-\phi^2} \quad (122)$$

Which is the self consistent equation we have. Combining the three terms, since $p = \langle n_{i\uparrow}n_{l\uparrow} \rangle + \langle S_i^+ S_l^- \rangle - \langle \Delta_i \Delta_l^* \rangle$, we obtain the following self consistent equation

$$p = \frac{n^2}{4} - \frac{\rho_1}{1-\phi^2} - \frac{\rho_1}{1-\phi} - \frac{\rho_3}{1+\phi} \quad (123)$$

APPENDIX E: BANDS AT AND AROUND HALF-FILLING

Here we plot the bands for nearest-neighbors at half filling for the 3 minimization. We see the Fermi

energy in between the two bands therefore we have an insulator. Note we get the same result with next-nearest neighbors. We plot the bands for Roth solution at 2% hole doping with its Fermi Surface: we see the formation of a small hole pocket at (π, π) when approaching half filling. This can be interpreted as a magnetic instability [17], our assumption of paramagnetism becomes invalid.

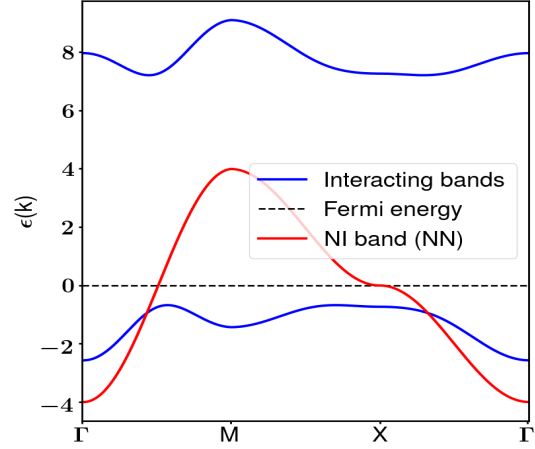


Figure 17: Band at half filling with $t=1$, $U=8t$. Note that all three solutions (COM2 and Roth) are alike.

APPENDIX F: ROTH DECOUPLING WITH SUPERCONDUCTIVITY

In this appendix we show how Roth decoupling changes when we include superconductivity with 4x4 basis. We will redo one of the terms of p as an example, and perform the decoupling for the θ parameter. Let us start by considering $\langle S_i^- S_l^+ \rangle$ in p for example. The superconducting basis is of size 4 and define by

$$\psi = \begin{pmatrix} \xi_{i\uparrow} \\ \eta_{i\uparrow} \\ \xi_{i\downarrow}^\dagger \\ \eta_{i\downarrow} \end{pmatrix} \quad (124)$$

To include the full basis we need to introduce 4 Green's functions now

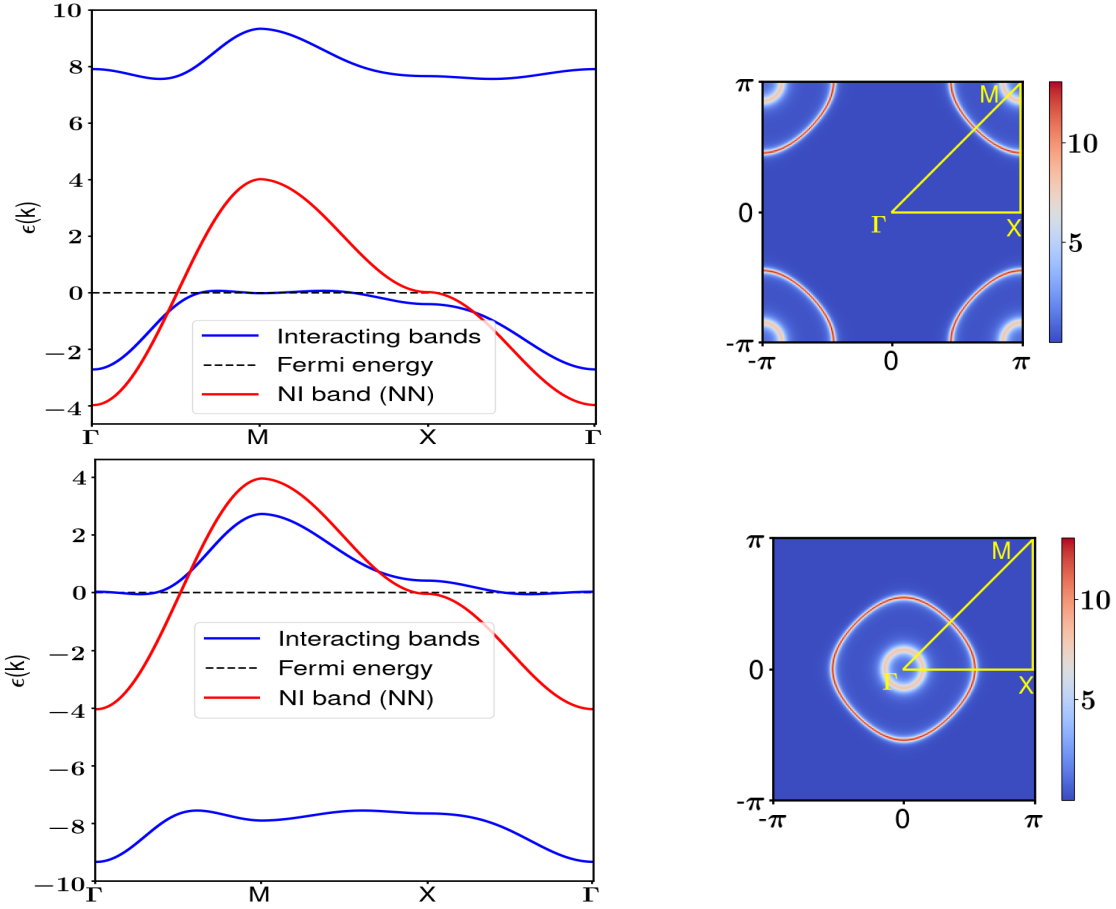


Figure 16: Fermi Surfaces and bands obtained by Pauli minimization in the neighborhood of half filling. Top row: 2% hole doped. Bottom row: 2% electron doped.

$$\begin{aligned}
 A_{ijl} &= \langle \langle \xi_{i\uparrow}; c_{j\downarrow}^\dagger S_l^+ \rangle \rangle \\
 B_{ijl} &= \langle \langle \eta_{i\uparrow}; c_{j\downarrow}^\dagger S_l^+ \rangle \rangle \\
 F_{ijl} &= \langle \langle \xi_{i\downarrow}; c_{j\downarrow}^\dagger S_l^+ \rangle \rangle \\
 G_{ijl} &= \langle \langle \eta_{i\downarrow}; c_{j\downarrow}^\dagger S_l^+ \rangle \rangle
 \end{aligned} \tag{125}$$

Now the equations of motion has to be defined for the 4 Green's functions. Hence

$$\partial_\tau \begin{pmatrix} A_{ijl} \\ B_{ijl} \\ F_{ijl} \\ G_{ijl} \end{pmatrix} (\tau) = \sum_k E_{ik} \begin{pmatrix} A_{ijl} \\ B_{ijl} \\ F_{ijl} \\ G_{ijl} \end{pmatrix} (\tau) + \delta(\tau) \begin{pmatrix} f_{ijl}^1 \\ f_{ijl}^2 \\ f_{ijl}^3 \\ f_{ijl}^4 \end{pmatrix} \tag{126}$$

With $f_{ijl}^n = \langle \langle \psi_i^n; c_{j\downarrow}^\dagger S_l^+ \rangle \rangle$. As before we can use $(\omega - E_{ik}) = S_{ik}(\omega)I^{-1}$ and integrate over ω after we

took the imaginary part to replace the composite Green's function matrix by a correlation function matrix. Thus

$$\begin{aligned}
 -\langle c_{j\downarrow}^\dagger c_{i\uparrow} S_l^+ \rangle &= \frac{2}{2-n} \sum_k [(C_{ik}^{11} + C_{ik}^{12})f_{kjl}^1 + (C_{ik}^{12} + C_{ik}^{22})f_{kjl}^2 \\
 &\quad + (C_{ik}^{13} + C_{ik}^{23})f_{kjl}^3 + (C_{ik}^{14} + C_{ik}^{24})f_{kjl}^4]
 \end{aligned} \tag{127}$$

In the last equation, the first line is the same as before, while the second line are additional terms appearing with the superconducting basis. A bit of algebra yields to

$$\begin{aligned}
 f_{kjl}^3 &= \delta_{kl}(C_{kj}^{13} + C_{kj}^{14}) \\
 f_{kjl}^4 &= \delta_{kl}(C_{kj}^{23} + C_{kj}^{24})
 \end{aligned} \tag{128}$$

Finally the spin-spin term in p becomes

$$\langle S_i^- S_l^+ \rangle = -\frac{\rho_1 + \rho_2}{1 - \phi} \quad (129)$$

With $\rho_2 = \frac{2}{2-n}(C_{il}^{13} + C_{il}^{14})^2 + \frac{2}{n}(C_{il}^{23} + C_{il}^{24})^2$.

Now we move on to the Roth decoupling for θ . As Beenen and Edwards [10] have mentioned, we have several ways of decoupling θ depending on whether we consider $\langle c_{i\uparrow} c_{i\downarrow} n_{l\sigma} \rangle$ or for example $\langle c_{i\downarrow}^\dagger c_{i\uparrow}^\dagger n_{l\sigma} \rangle$. Depending on the decoupling scheme we will over estimate or underestimate the real value of θ but the behaviour will remain globally the same [22]. Here we consider a decoupling starting from $\langle \langle c_{i\downarrow}^\dagger, c_{i\uparrow}^\dagger n_{l\sigma} \rangle \rangle$. We introduce the following Green's functions

$$\begin{pmatrix} A_{ijl} = \langle \langle \xi_{i\uparrow}; c_{j\uparrow}^\dagger n_{l\uparrow} \rangle \rangle \\ B_{ijl} = \langle \langle \eta_{i\uparrow}; c_{j\uparrow}^\dagger n_{l\uparrow} \rangle \rangle \\ F_{ijl} = \langle \langle \xi_{i\downarrow}^\dagger; c_{j\uparrow}^\dagger n_{l\uparrow} \rangle \rangle \\ G_{ijl} = \langle \langle \eta_{i\downarrow}^\dagger; c_{j\uparrow}^\dagger n_{l\uparrow} \rangle \rangle \end{pmatrix} \quad (130)$$

The decoupling is identical and by considering F+G we arrive to

$$\begin{aligned} \langle c_{i\downarrow}^\dagger c_{j\uparrow}^\dagger n_{l\sigma} \rangle &= \frac{2}{2-n} \sum_k [(C_{ik}^{13} + C_{ik}^{14}) f_{kjl}^1 + (C_{ik}^{33} + C_{ik}^{44}) f_{kjl}^3] \\ &+ \frac{2}{n} \sum_k [(C_{ik}^{23} + C_{ik}^{24}) f_{kjl}^2 + (C_{ik}^{34} + C_{ik}^{44}) f_{kjl}^4] \end{aligned} \quad (131)$$

With $f_{kjl}^n = \langle \langle \psi_k^n; c_{j\uparrow}^\dagger n_{l\sigma} \rangle \rangle$. Computing the f gives

$$\begin{aligned} f_{kjl}^1 &= \delta_{kj} \left(\frac{n}{2} - \langle n_{k\uparrow} n_{l\uparrow} \rangle \right) + \delta_{kl} (C_{kj}^{11} + C_{kj}^{12}) \\ f_{kjl}^2 &= \delta_{kj} \langle n_{k\uparrow} n_{l\uparrow} \rangle + \delta_{kl} (C_{kj}^{12} + C_{kj}^{22}) \\ f_{kjl}^3 &= -\delta_{kj} \frac{\theta_{kl}}{2} \\ f_{kjl}^4 &= \delta_{kj} \frac{\theta_{kl}}{2} \end{aligned} \quad (132)$$

We therefore obtain

$$\begin{aligned} \frac{\theta}{2} &= \frac{\langle n_{i\uparrow} n_{l\uparrow} \rangle \left[\frac{2}{n} (C_0^{23} + C_0^{24}) - \frac{2}{2-n} (C_0^{13} + C_0^{14}) \right] + \zeta}{1 + \phi} \\ &+ \frac{n C_0^{13} + C_0^{14}}{2(1 + \phi)} \end{aligned} \quad (133)$$

With $\zeta = \frac{2}{2-n}(C_{il}^{11} + C_{il}^{12})(C_{il}^{13} + C_{il}^{14}) + \frac{2}{n}(C_{il}^{12} + C_{il}^{22})(C_{il}^{23} + C_{il}^{24})$. Finally by noting that $C_0^{23} + C_0^{24} = 0$ and $C_0^{13} + C_0^{14} = 0$, we obtain the equation we used

$$\frac{\theta}{2} = \frac{\zeta}{1 + \phi} \quad (134)$$

APPENDIX G: EFFECTS OF PARTICLE-HOLE TRANSFORMATION

In this appendix we give some details on how we derived the particle-hole relations in Eq. (55). The relation for the chemical potential is obtained by using the fact that the Hubbard hamiltonian stays invariant under this transformation.

$$\begin{aligned} H &= \sum_{ij\sigma} t_{ij} c_{i\sigma}^\dagger c_{j\sigma} + U \sum n_{i\uparrow} n_{i\downarrow} + \mu \sum_{i\sigma} n_{i\sigma} \\ &\rightarrow \sum_{ij\sigma} t_{ij} (-1)^{i+j} c_{i\sigma} c_{j\sigma}^\dagger + U \sum_i (-1)^{4i} c_{i\uparrow} c_{i\uparrow}^\dagger c_{i\downarrow} c_{i\downarrow}^\dagger \\ &- \mu \sum_{i\sigma} (-1)^{2i} c_{i\sigma} c_{i\sigma}^\dagger \\ &= -\sum_{ij\sigma} t_{ij} c_{i\sigma} c_{j\sigma}^\dagger + U \sum_i (c_{i\downarrow} c_{i\downarrow}^\dagger - n_{i\uparrow} c_{i\downarrow} c_{i\downarrow}^\dagger) + \mu \sum_{i\sigma} n_{i\sigma} \\ &= \sum_{ij\sigma} t_{ij} c_{j\sigma}^\dagger c_{i\sigma} + U \sum_i (1 - n_{i\downarrow} - n_{i\uparrow} + n_{i\uparrow} n_{i\downarrow}) + \mu \sum_{i\sigma} n_{i\sigma} \\ &= \sum_{ij\sigma} t_{ij} c_{i\sigma}^\dagger c_{j\sigma} + U \sum_i n_{i\uparrow} n_{i\downarrow} + (\mu - U) \sum_{i\sigma} n_{i\sigma} + cste \end{aligned} \quad (135)$$

Thus, to keep the Hamiltonian invariant and therefore have under the particle-hole transformation $H \rightarrow H$, we need to impose

$$\mu(2 - n) = -(\mu(n) - U) \quad (136)$$

Which is the relation we get in the main text. For e and p we work directly with their definitions

$$\begin{aligned} e &= \langle \xi_{i\sigma} \xi_{j\sigma}^\dagger \rangle - \langle \eta_{i\sigma} \eta_{j\sigma}^\dagger \rangle \\ p &= \langle n_{i\sigma} n_{j\sigma} \rangle + \langle S_i^+ S_j^- \rangle - \langle \Delta_i \Delta_j^* \rangle \end{aligned} \quad (137)$$

Under the particle-hole transformation we have

$$\xi_{i\sigma} \rightarrow (-1)^i \eta_{i\sigma}^\dagger \quad \eta_{i\sigma} \rightarrow (-1)^i \xi_{i\sigma}^\dagger \quad (138)$$

Hence

$$\begin{aligned} e(2 - n) &\rightarrow (-1)^{i+j} (\langle \eta_{i\sigma}^\dagger \eta_{j\sigma} \rangle - \langle \xi_{i\sigma}^\dagger \xi_{j\sigma} \rangle) \\ &= \langle \eta_{j\sigma} \eta_{i\sigma}^\dagger \rangle - \langle \xi_{j\sigma} \xi_{i\sigma}^\dagger \rangle \\ &= -(\langle \xi_{i\sigma} \xi_{j\sigma}^\dagger \rangle - \langle \eta_{i\sigma} \eta_{j\sigma}^\dagger \rangle) \\ &= -e(n) \end{aligned} \quad (139)$$

We didn't kept the terms with δ_{ij} because e and p always appear with a t_{ij} prefactor and $t_{ij} = 0$ if $i = j$. We used the fact that i and j are always nearest-neighbours to get $(-1)^{i+j} = -1$. For p we have

$$\begin{aligned}
p &\rightarrow (-1)^{2i+2j} \langle c_{i\sigma} c_{i\sigma}^\dagger c_{j\sigma} c_{j\sigma}^\dagger + c_{i\uparrow} c_{i\downarrow}^\dagger c_{j\downarrow} c_{j\uparrow}^\dagger \\
&\quad - c_{i\uparrow}^\dagger c_{i\downarrow}^\dagger c_{j\downarrow} c_{j\uparrow} \rangle \\
&= \langle c_{j\sigma} c_{j\sigma}^\dagger - n_{i\sigma} c_{j\sigma} c_{j\sigma}^\dagger + S_i^- S_j^+ - \Delta_j^* \Delta_i \rangle \\
&= \langle 1 - n_{j\sigma} - n_{i\sigma} + n_{i\sigma} n_{j\sigma} + S_j^+ S_i^- - \Delta_i \Delta_j^* \rangle \\
&= 1 - \frac{n}{2} - \frac{n}{2} + p(n) \\
&= (1 - n) + p(n)
\end{aligned} \tag{140}$$

Which is the other relation we had.